



# SSQS

**Samsung Shipbuilding Quality Standard**

# Samsung Shipbuilding Quality Standard 2005

- ☐ CONTROLLED COPY    NO. \_\_\_\_\_
- ☐ UNCONTROLLED COPY

**SAMSUNG  
HEAVY INDUSTRIES**

**SAMSUNG**

<http://www.shi.samsung.co.kr>

# CONTENTS

HISTORY .....	3
PREFACE .....	4

## PART A. QUALITY STANDARD

I . HULL PART	
1. Material .....	6
2. Welding .....	10
3. Marking .....	14
4. Cutting .....	15
5. Fabrication .....	16
6. Accuracy of hull form .....	19
7. Deformation .....	19
8. Details .....	23
9. Surface finish condition .....	29
10. Marking on ship side .....	30
II . PAINTING PART	
1. Primary surface preparation and pre-priming .....	31
2. Secondary surface preparation .....	31
3. Painting .....	34
4. Ambient condition .....	35
5. D.F.T Measurement .....	35
6. Time for D.F.T Measurement .....	36
III . OUTFITTING PART	
1. Main machinery .....	37
2. Auxiliary machinery .....	43
3. Piping .....	45
4. Sheet metal outfitting .....	56

## PART B. SCOPE OF INSPECTION

I . HULL .....	61
II . HULL OUTFITTING .....	62
III . MACHINERY .....	64
IV . PIPING .....	69
V . ELECTRIC .....	70
VI . PAINTING .....	73

---

## HISTORY

---

<b>Sep.</b>	<b>1979.</b>	<b>The First Edition</b>
<b>Jan.</b>	<b>1984.</b>	<b>The First Revision</b>
<b>Mar.</b>	<b>1986.</b>	<b>The Second Revision</b>
<b>Jun.</b>	<b>1988.</b>	<b>The Third Revision</b>
<b>Jun.</b>	<b>1990.</b>	<b>The Fourth Revision</b>
<b>Oct.</b>	<b>1992.</b>	<b>The Fifth Revision</b>
<b>May.</b>	<b>1994.</b>	<b>The Sixth Revision</b>
<b>Sep.</b>	<b>1996.</b>	<b>The Seventh Revision</b>
<b>Apr.</b>	<b>2000.</b>	<b>The Eighth Revision</b>
<b>Jan.</b>	<b>2005.</b>	<b>The Ninth Revision</b>

# P R E F A C E

This Samsung Shipbuilding Quality Standard(SSQS) is compiled in an effort to standardize the production and quality control practices for the building of new vessels in Samsung Heavy Industries Co., Ltd.

Considering the importance of the quality control in the shipbuilding industry, the process control policy has been emphasized as the basic quality control policy to minimize potential defects at each production stage and to assure the quality of the final products.

This booklet consists of two sections ;

- Quality Standard
- Scope of Inspection

The Standard mentioned in the booklet will be generally applied to the quality control of the shipbuilding at the Geoje Shipyard.

## **PART A. QUALITY STANDARD**

### **I . HULL PART ..... 6**

1. Material
2. Welding
3. Marking
4. Cutting
5. Fabrication
6. Accuracy of hull form
7. Deformation
8. Details
9. Surface finish condition
10. Marking on ship side

### **II . PAINTING PART ..... 31**

1. Primary surface preparation and pre-priming
2. Secondary surface preparation
3. Painting
4. Ambient condition
5. D.F.T Measurement
6. Time for D.F.T Measurement

### **III . OUTFITTING PART ..... 37**

1. Main machinery
2. Auxiliary machinery
3. Piping
4. Sheet metal outfitting

# **I. HULL PART**

## **1. MATERIAL**

### **1-1. Rolled plate**

#### **1-1-1. Definition of imperfection and defect**

- An imperfection is some feature which introduces an irregularity in an otherwise uniform structure.
- A defect is a specific imperfection which impairs the suitability of that structure for its intended purpose.

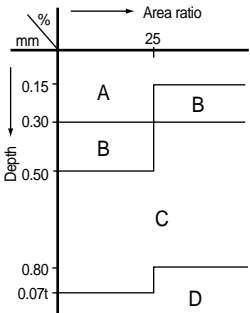
In order to determine if a particular imperfection is actually a defect, there must be some standard which defines the acceptable limits of that imperfection. When its size or concentration exceeds these limits, it is deemed a defect. We can therefore think of a defect as simply a rejectable imperfection.

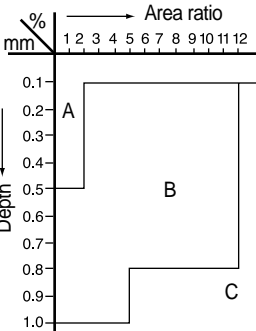
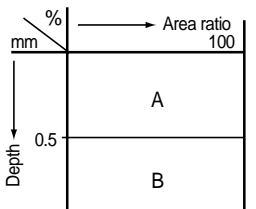

Imperfections related to the following discontinuities.

: Pitting, rolled in scale, indentations, roll marks, scratches and grooves

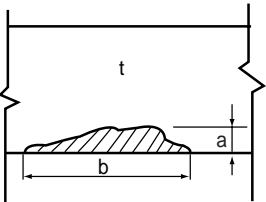


Defects related to the following discontinuities.

: Cracks, shells, seams, spills, blisters, hot tears and sand patches

Object		Detail	Correction / Remarks
1-1-2. Surface Imper- fections	Pit	<p data-bbox="361 211 572 249">Grade of pitting</p>  <p data-bbox="366 756 628 831"> <math display="block">\text{Area ratio (\%)} = \frac{\text{Area of pitting}}{\text{Total area of steel surface}} \times 100</math> </p>	<ol style="list-style-type: none"> <li>1. Grade A : Repair is unnecessary.</li> <li>2. Grade B :             <ol style="list-style-type: none"> <li>1) Outer surface of shell plates: To be repaired by grinding (if necessary) (When painting with epoxy can not be done, grinding is to be carried out.)</li> <li>2) Others : Repair is unnecessary.</li> </ol> </li> <li>3. Grade C :             <ol style="list-style-type: none"> <li>1) Outer surface of shell plates : To be repaired by grinding</li> <li>2) Others : Painting with epoxy to be carried out</li> </ol> </li> <li>4. Grade D: Repair method is to be determined after discussion with owner and class.             <ul style="list-style-type: none"> <li>* Recommended repair method : Grinding followed by welding</li> </ul> </li> <li>5. The ground area shall not exceed the tolerances as follows.             <ol style="list-style-type: none"> <li>1) Single ground area : 0.25 m<sup>2</sup></li> <li>2) Total ground area : 2% of the total surface area</li> </ol> </li> <li>6. Repaired area by welding shall not exceed :             <ol style="list-style-type: none"> <li>1) Single ground area : 0.125 m<sup>2</sup></li> <li>2) Total ground area : 2% of the total surface area of the side involved</li> </ol> </li> </ol>

Object		Detail	Correction / Remarks
1-1-2. Surface Imperfections	Flaking	<p>Grade of surface flaking</p> 	<p>1. Grade A : Repair is unnecessary.  Grade B : To be repaired if necessary  Grade C : To be repaired</p> <p>2. Repair method  Depth of defects : <math>d</math>  Plate thickness : <math>t</math>  1) <math>d &lt; 0.07t</math> (max. 3mm) ... Removed by grinding  2) <math>0.07t \leq d \leq 0.2t</math> ... Grinding followed by welding  (The welded area should be less than 2% of the total surface area.)</p>
	Indentation (other defects)	<p>Grade of indentation</p>  	<p>1. Grade A : Repair is unnecessary.  Grade B : Repair is necessary.</p> <p>2. Repair method  Depth of defects : <math>d</math>  Plate thickness : <math>t</math>  1) <math>d &lt; 0.07t</math> (max. 3mm) : Grinding  2) <math>0.07t \leq d \leq 0.2t</math> : Welding and grinding</p> <p>3. The welded area should be less than 2% of the total area of a plate.</p>



Object	Detail	Correction / Remarks
1-1-3. Lamination	<p>Local lamination</p> <p><math>a \leq 1t</math></p>  <p><i>"b" is the length of the defect on the flame-cut edge. "a" is the other dimension. "t" is the plate thickness.</i></p>	<p>In case where the range of lamination is limited, it can be chipped out and built-up by welding as shown in (a).</p> <p>(a) </p> <p>In case where the range of lamination is limited, but is also near the plate surface, it is preferable to make the built-up welding as shown in (b).</p> <p>(b) </p> <p>It must be carefully examined whether the procedure is acceptable or not, in case where the degree of the lamination is more severe and defective.</p>
	<p>Severe lamination requiring a local exchange of plate</p> <p><math>a &gt; 1t</math></p>	<p>It is recommended to exchange locally the plate, in case where the range of lamination is fairly extensive. The standard minimum breadth of plate to be exchanged :</p> <p>Shell and strength deck plating in way of cruciform or T-joints ..... 1,600mm</p> <p>Shell, strength deck plating and other primary members ..... 800mm</p> <p>Other structural members ..... 300mm</p>







## 1-2. Cast steel

Object	Detail	Correction / Remarks
Defects of cast steel	<p>In case where examined defect is over 20% of thickness, or over 25mm deep and 150mm long</p>	<p>In case where cavity, crack and other injurious defects are found,</p> <ol style="list-style-type: none"> <li>1) Remove the defects by gouging.</li> <li>2) Gouged areas shall be welded in accordance with maker's recommendation and/or an approved WPS.</li> <li>3) Repaired areas shall be checked by magnetic particle testing or ultrasonic testing.</li> </ol>


## 2. WELDING

### 2-1. Shape of bead

Unit : mm

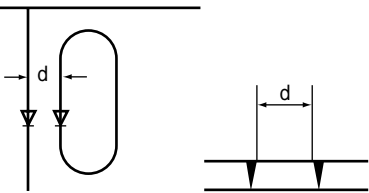

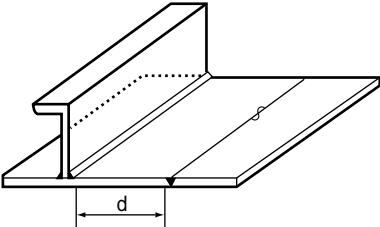
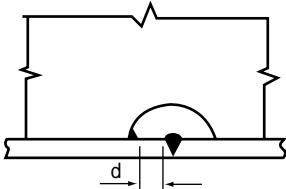
Item	Details		Tolerance limits	Remarks
2-1-1. Over-lap	Butt		$\theta \leq 90^\circ$	In case $\theta > 90^\circ$ , grinding or welding is necessary to make $\theta \leq 90^\circ$ .
	Fillet			
2-1-2. Under cut	Butt		$d \leq 0.5$ (Length of less than 90mm continuous)	Where $0.5 < d \leq 1$ undercut to be ground smooth (Localised only) Where $d > 1$ undercut to be filled by welding (Carefully avoid short bead for high tensile steels)
	Fillet			
2-1-3. Leg length and throat			$L \geq L_0$ $t \geq t_0$ If $0.9L_0 \leq L < L_0$ or $0.9t_0 \leq t < t_0$ , the extent is to be less than 10%	$L_0$ : Designed leg length $t_0$ : Designed throat
Item	Details		Standard range	Tolerance limits
2-1-4. Height of reinforcement			$h \leq 0.2R$	max. $h = 6$

Unit : mm

Item	Details	Tolerance limits	Corrections / remarks
2-1-5. Irregularity of multi weld		$h \leq 3$	<p>When the surface irregularity exceeds 3mm, apply grinding until the irregularity becomes less than 3mm. (This repair standard is applicable to fillet welds also)</p>

# 2-2. Preparation of welding

Unit : mm

Item	Details		Tolerance limits	Remarks
2-2-1. Distance between two butt welds			$d \geq 30$	
			$d \geq 0$	
2-2-2. Distance between butt weld and fillet weld		Main structure	$d \geq 10$	
		Other structure	$d \geq 0$	
		Main structure	$d \geq 5$	
		Other structure	$d \geq 0$	

## 2-3. Short bead

Unit : mm

Item	Details	Tolerance limits	Corrections / remarks
2-3-1. Damage part of base metal	• Normalized 50HT	$\geq 50$	<p>* In case where short bead is used unavoidably, preheating is necessary at <math>100 \pm 25^{\circ}\text{C}</math>.</p> <p>* Where short bead is made erroneously, remove the bead by grinding, and weld over tolerable bead length after confirming crack.</p>
	• Cast steel	$\geq 30$	
	• Mild steel	$\geq 10$	
2-3-2. Repair part of welding bead and tack welding	• TMCP 50HT (Ceq. $\leq 0.36\%$ )	$\geq 10$	
	• Normalized 50HT	$\geq 50$	
	• Cast steel	$\geq 30$	
	• Mild steel		
	• TMCP 50HT (Ceq. $\leq 0.36\%$ )		

## 2-4. Repair of arc strike

Details	Tolerance limits	Corrections
<ul style="list-style-type: none"> <li>• Normalized 50HT</li> <li>• Cast steel</li> <li>• TMCP 50 HT</li> <li>• Grade E of mild steel</li> </ul>	Prohibited	In case where arc strike is made erroneously, remove the hardened zone by grinding



## 2-5. Pre-heating

Details	Limits of atmospheric temperature	min. preheating temperature
<ul style="list-style-type: none"> <li>• Mild steel</li> <li>• TMCP 50HT (Ceq. <math>\leq 0.36\%</math>)</li> </ul>	$T \leq -5^{\circ}\text{C}$	min. $50^{\circ}\text{C}$
<ul style="list-style-type: none"> <li>• Normalized 50HT</li> </ul>	$T \leq 5^{\circ}\text{C}$	min. $50^{\circ}\text{C}$
<p>* Remark : 1. When Ceq. of touched metals is different, the higher Ceq. has to be taken.  2. Cast steel &amp; all other steel grades, specific temperature of Cast steel shall be followed by approved WPS independently atmospheric temperature, if required in approved WPS.</p>		

### 3. MARKING



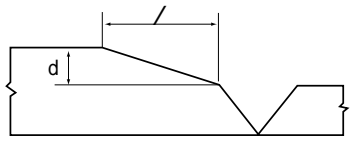
#### 3-1. Cutting line and fitting line

Unit : mm

Section	Item	Standard range	Tolerance limits	Remarks
3-1. Cutting line and fitting line	Size and shape	$\pm 1.0$	$\pm 2.5$	
	Straightness 	$\pm 1.0$	$\pm 1.5$	min. $\neq 5m$
	Location of member and mark for fitting 	$\neq \pm 2.0$	$\neq \pm 3.0$	







## 4. CUTTING

Unit : mm

Section	Item			Standard range	Tolerance limits
4-1. Notch	Free edge	1) Upper edge of sheer strake 2) Free edge of strength deck within 0.6 L $\oslash$ and opening of shell plate 3) Main longitudinal strength members		-	Not allowed
		Longitudinal and transverse strength members		-	Ind. $\leq 1$
		Other		-	Ind. $\leq 3$
	Weld groove	Butt Weld	$w \leq 3$		Ind. $\leq 1.5$
			$w > 3$		Ind. $\leq 2.5$
		Fillet weld		-	Ind. $\leq 3$
4-2. Dimension	Straightness of plate edge	Both side submerged arc welding		$\pm 0.4$	$\pm 0.5$
		Manual welding, semi automatic welding		$\pm 1.0$	$\pm 2.5$
	Depth of groove	Deviation of $\angle$ and $\angle$ between designed depth and actual depth 		$\pm 1.5$	$\pm 2.0$
	Length of taper	Deviation of $\angle$ between designed length and actual length 		$3d \pm 0.5d$	$3d \pm 1.0d$
	Size of member	General members compared with correct size		$\pm 3.5$	$\pm 5.0$
		Especially for the depth of floor and girder of double bottom compared with correct size		$\pm 2.5$	$\pm 4.0$
		Breadth of face bar compared with correct size		$\pm 2.0$	$-3.0 \sim +4.0$




## 5. FABRICATION

Unit : mm

Section	Subsection	Item	Standard range	Tolerance limits	Remarks
5-1. Flanged longitudinal	Breadth of flange and web	 Compared with correct size	$\pm 3.0$	$\pm 5.0$	
	Angle between flange and web	 Compared with template	$\pm 2.5$ per 100	$\pm 4.5$ per 100	
	Curvature or straightness in the plane of flange	 per 10m in length	$\pm 10$	$\pm 25$	
	Curvature or straightness in the plane of web	 per 10m in length	$\pm 10$	$\pm 25$	
5-2. Flanged bracket	Breadth of flange	 Compared with correct size	$\pm 3.0$	$\pm 5.0$	
	Angle between flange and web	 Compared with template	$\pm 3.0$ per 100	$\pm 5.0$ per 100	



Unit : mm


Section	Subsection	Item	Standard range	Tolerance limits	Remarks
5-3. Built-up sections	Distortion of face plate		$a = 2 + \frac{b}{100}$	$a = 5 + \frac{b}{100}$	
	Deviation of squareness between face plate and web		$\pm 1.5$ per 100	$\pm 3.0$ per 100	
	Longitudinal and transverse distortion at face plate and web		$\pm 5$	$\pm 8$	per span between primary members

#### 5-4. Line heating

Section	Item		Standard range	Remarks
Max. heating temperature on surface	<ul style="list-style-type: none"> <li>Normalized 50HT</li> </ul>	Water cooling just after heating	under 650°C	
		Air cooling after heating	under 900°C	
		Air cooling and subsequent water cooling after heating	under 900°C (Starting temperature of water cooling to be under 500°C )	
	TMCP 50HT (Ceq. ≤ 0.36%) AH, DH	Water cooling just after heating or air cooling	under 1000°C	Within 3 cycles as far as practicable
	TMCP 50HT (Ceq. ≤ 0.36%) EH	Water cooling just after heating or air cooling	under 900°C	Within 2 cycles as far as practicable
	* Note : Air cooling means by compressed air. Heating means by flame torch.			

## 6. ACCURACY OF HULL FORM


Unit : mm

Item	Details	Standard range	Remarks
Length	Length between perpendiculars	$\pm 50$ per 100m	Applied to ships of 100m length and above. For the convenience of the measurement, the point where the keel is connected to the curve of the stem may be substituted for the fore perpendicular in the measurement of the length.
Breadth	Moulded breadth amidship	$\pm 15$	Applied to ships of 15 meter breadth and above. To be measured on the upper deck.
Depth	Moulded depth amidship	$\pm 10$	Applied to ships of 10 meter depth and above.
Flatness of keel	Deformation for the whole length 	$\pm 25$	Up (-) and Down (+) against the check line of keel sighting.

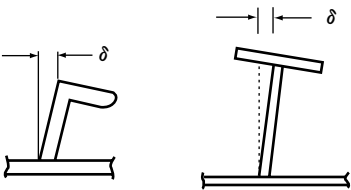
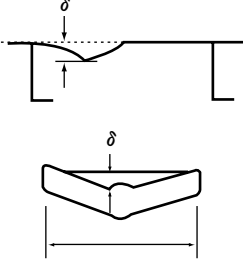
## 7. DEFORMATION



### 7-1. Deformation

Unit : mm

Area	Item	Standard range	Tolerance limits	Remarks
Shell plate	Parallel part (side shell)	$\pm 4$	$\pm 7$	For length of frame space, longi. space, stiffener space, any of the above is not applicable for over 1.8m length.
	Parallel part (bottom shell)	$\pm 4$	$\pm 7$	
	Fore and aft part	$\pm 5$	$\pm 7$	
Double bottom tank top plate		$\pm 4$	$\pm 7$	
Bulkhead	Longi. bulkhead, trans-bulkhead & swash bulkhead	$\pm 6$	$\pm 8$	

Unit : mm



Area	Item	Standard range	Tolerance limits	Remarks
Strength deck	Parallel part (Between 0.6L amidship)	$\pm 4$	$\pm 7$	
	Fore and aft part	$\pm 6$	$\pm 9$	
	Covered part	$\pm 7$	$\pm 9$	
Second deck	Bare part	$\pm 6$	$\pm 8$	
	Covered part	$\pm 7$	$\pm 9$	
Forecastle deck, poop deck	Bare part	$\pm 4$	$\pm 7$	
	Covered part	$\pm 6$	$\pm 9$	
Superstructure deck	Bare part	$\pm 4$	$\pm 6$	
	Covered part	$\pm 7$	$\pm 9$	
House wall	Outside wall	$\pm 4$	$\pm 7$	
	Inside wall	$\pm 6$	$\pm 8$	
	Covered part	$\pm 7$	$\pm 9$	
Interior member	Web of girder, trans.	$\pm 5$	$\pm 7$	
Floor and girder of double bottom		$\pm 5$	$\pm 7$	
Unfairness of interior members after welding (beam, frame, stiffener, floor girder, etc.)		-	$\leq 8$	
Angular distortion of welding joint after welding 	Skin plate between 0.6L amidship	-	$\leq 6$	
	Fore and aft shell plating and transverse strength member	-	$\leq 7$	
	Span of frame or beam	-	$\leq 8$	

Item	Details		Standard range	Tolerance limits	Remarks	
H-type Pillar	Distortion between decks		$\pm 4$	$\pm 6$		
Tripping bracket and small stiffener	Distortion at the part of free edge		$a \leq t/2$	max. 8		
Vehicles loading apparatus	Hoistable deck (Liftable deck)	Deflection of deck $\delta_1$		+5 0		
		Deformation of deck	$\delta_2$	+5		+10
			$\delta_3$	-2		-5
	Stern ramp	Transverse and longitudinal deflection $\delta_4$		-	$\pm 5$	$\delta_4, \delta_5$ to be measured on the top plate of girder
	Midship ramp	Transverse and longitudinal deflection $\delta_5$		-	$\pm 5$	
	Bulkhead door	Transverse and longitudinal deflection $\delta_6$		-	$\pm 3$	$\delta_6$ = actual measurement value
	Fixed ramp			$\pm 6$	$\pm 8$	

Remarks : Maker's instruction shall prevail regarding the above deformation of ramps.






## 7-2. Deformation per basic length



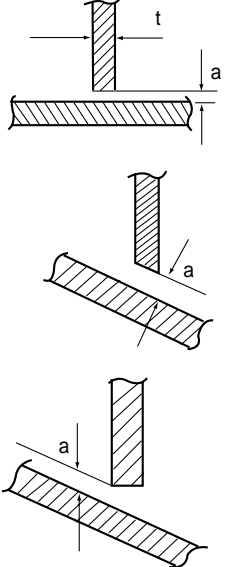
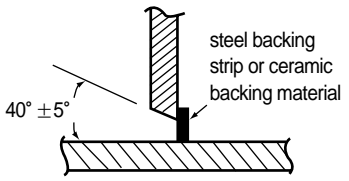
Unit : mm

Area	Item	Standard range	Tolerance limits	Remarks
Shell plate	Parallel part	$\pm 2 // 1000$	$\pm 3 // 1000$	 
	Fore and aft part	$\pm 3 // 1000$	$\pm 4 // 1000$	
Deck and top plate of double bottom	-	$\pm 3 // 1000$	$\pm 4 // 1000$	<ul style="list-style-type: none"> <li>• To be measured between one trans. space (min. <math>\neq 3\text{m}</math>)</li> <li>• Measured length is about 5m for bulk-head, outside wall etc.</li> </ul>
Bulkhead	-	$\pm 4 // 1000$	$\pm 5 // 1000$	
Accommodation	Deck	$\pm 3 // 1000$	$\pm 4 // 1000$	
	Outside wall	$\pm 2 // 1000$	$\pm 3 // 1000$	
Others	-	$\pm 5 // 1000$	$\pm 6 // 1000$	

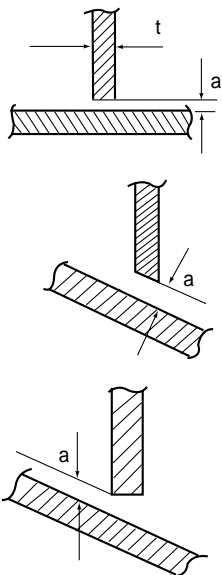
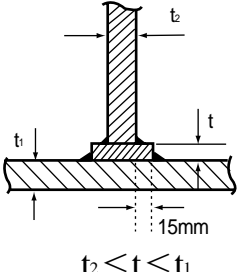
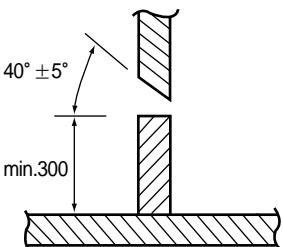
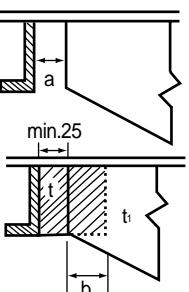
## 8. DETAILS






Unit : mm

Object		Detail	Tolerance limits	Corrections / Remarks
8-1. Misalignment between components on each side of through going component		 $t_1 \leq t_2$	Strength members $a \leq \frac{t_1}{3}$ Others $a \leq \frac{t_1}{2}$	1. $\frac{t_1}{3} < a \leq \frac{t_1}{2}$ (in case of strength member) the weld throat to be increased by 10% 2. $a > \frac{t_1}{2}$ Position to be adjusted. adjustment length $L \geq 50 \times a$
8-2. Misalignment in block/section joint (Shell plate, deck, bottom, inner bottom, bulkhead, etc.)		 $t_1 \leq t_2$	Strength members $a \leq 0.15t_1$ (max. 3) Others $a \leq 0.2t_1$ (max. 3)	The plates are to be adjusted.
8-3. Misalignment in joints between longitudinal profiles.	web		Primary members $a \leq 0.15t$ (max. 3) Secondary members $a \leq 0.2t$ (max. 3)	Adjustment length $L \geq 30 \times a$ or adjustment by welding
	Flange		$a \leq 0.04b$ (max.8)	When $0.04b < a \leq 8$ , grind corners to smooth taper over distance min. $L=3a$ When $a > 8$ , release and adjust the plate min. $L=50a$
	Height of web		$a \leq 3$	1. $3 < a \leq 6$ Make a smooth shape by build-up. 2. $a > 6$ Release and adjust over min. $L=50a$ for primary structure and $L=30a$ elsewhere and weld after knuckling the flange.

Object	Detail	Tolerance limits	Corrections / Remarks
8-4. Overlap brackets		$a \leq 3$	<ol style="list-style-type: none"> <li><math>3 &lt; a \leq 5</math> Adjust before welding</li> <li><math>a &gt; 5</math> Release and adjust in length <math>L \geq 20 \times a</math></li> </ol>
8-5. Gap for overlap joint		$a \leq 3$	<ol style="list-style-type: none"> <li><math>3 &lt; a \leq 5</math>, increase leg length (Planned leg length + a)</li> <li><math>a &gt; 5</math>, Refitting</li> </ol>
8-6. Gap before welding of fillet joint	<p>Fillet weld</p> 	$a \leq 3$	<ol style="list-style-type: none"> <li>When <math>3 &lt; a \leq 5</math> The weld leg length to be increased as much as the gap opening exceeding 3mm  <math>L = L_0 + (a - 3)</math>  (L : Increased leg length  <math>L_0</math> : Designed leg length) </li> <li>When <math>5 &lt; a \leq 16</math> <ol style="list-style-type: none"> <li>1) Weld with bevel preparation to make bevel edge of web to <math>40^\circ \pm 5^\circ</math>, attach steel backing strip or ceramic backing material, and remove it after welding. Then, weld the opposite side after gouging.</li> </ol> </li> </ol> 

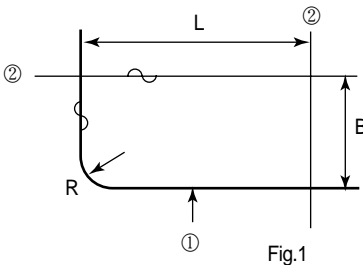
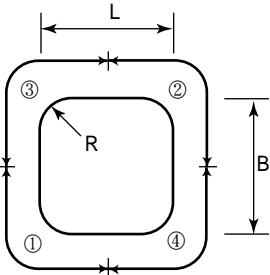
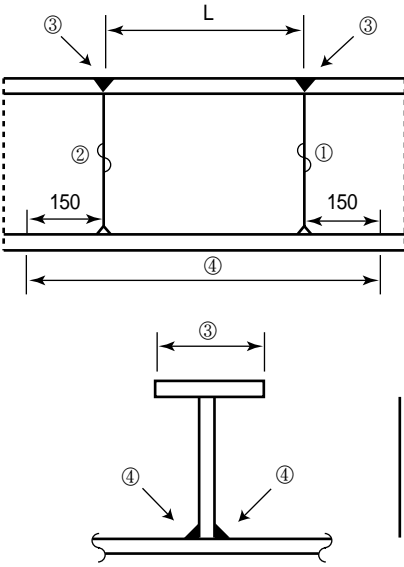


Object	Detail	Tolerance limits	Corrections / Remarks
8-6. Gap before welding of fillet joint		$a \leq 3$	<p>2) Liner treatment Subject to CLASS acceptance and not to be used in areas of tensile stress perpendicular to liner</p>  <p><math>t_2 \leq t \leq t_1</math></p> <p>3. When <math>a &gt; 16</math> Partial renewal</p>  <p><math>40^\circ \pm 5^\circ</math> min.300</p>
8-7. Gap before welding of joint between bracket/intercoastal and frame, beam, stiffener, etc. and in way of slot		$a \leq 3$	<p>1. When <math>3 &lt; a \leq 5</math>, the weld leg length to be increased as much as the gap opening exceeding 3.</p> <p>2. When <math>5 &lt; a \leq 10</math>, bevel <math>40^\circ \pm 5^\circ</math> and build up by welding.</p> <p>3. When <math>a &gt; 10</math>, fit the collar plate as shown in detail. <math>t \geq t_1</math>   <math>b : 2t + 25(\text{min.}50)</math>.</p>

Object	Detail	Tolerance limits	Corrections / Remarks
8-8. Butt joint	1. One side SAW 	$a \leq 3$	1. $3 < a \leq 8$ First or second pass by FCAW with ceramic backing 2. $a > 8$ Refitting or re-preparation after build-up
	2. Both side SAW 	$a \leq 1.5$	1. $1.5 < a \leq 5$ : Sealing bead is to be done. 2. $a > 5$ : Refitting
	3. FCAW 	$3.4 \leq a \leq 11.4$	1. $11.4 < a \leq 25$  Build-up the gap with welding on one or both sides of the preparation, with backing material to maximum gap of 11.0. 2. $a > 25$ Partial renewal 

## 8-9. Repair by insert plate

Unit : mm

Detail	Repair standard	Remarks
<p>8-9-1. Repair by insert plate</p>  <p>Fig.1</p>  <p>Fig.2</p>	<p> <math>L = \text{min. } 300</math>  <math>B = \text{min. } 300</math>  <math>R = 5 \times \text{Plate thickness and min. } 100</math> </p> <ol style="list-style-type: none"> <li>1) Seam with insert piece is to be welded first.</li> <li>2) Original seam is to be released and welded over for a min. 100.</li> <li>3) Welding sequence  <math>\textcircled{1} \rightarrow \textcircled{2} \rightarrow \textcircled{3} \rightarrow \textcircled{4}</math> </li> </ol>	
<p>8-9-2. Repair by built up section by insert plate</p> 	<p> <math>L = \text{min. } 300</math> </p> <ol style="list-style-type: none"> <li>1) Welding sequence  <math>\textcircled{1} \rightarrow \textcircled{2} \rightarrow \textcircled{3} \rightarrow \textcircled{4}</math> </li> <li>2) Web butt weld scallop to be filled during final pass <math>\textcircled{4}</math></li> </ol>	

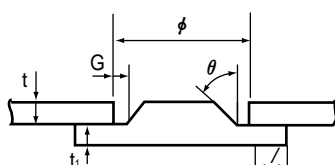
## 8-9-3. Treatment of hole made erroneously

(D : Diameter, B : Width of holes)

Sub-section	Item	Method	Remarks
D < 200 B < 300	Strength member in skin plate	㉑	Open the hole to over 75 $\phi$
		or ㉒	Open the hole to over 300 $\phi$
	Others	㉒㉓ or ㉔	
D $\geq$ 200 B $\geq$ 300	Strength member in skin plate	㉒	
	Others	㉒ or ㉓	
Serration, scallop, slot	-	㉒ or ㉓	

## Method of treatment

## ㉑ : Spigot patch



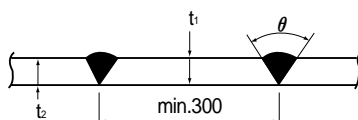
$$\theta = 40^\circ \pm 5^\circ$$

$$G = 4 \sim 6$$

$$t_1 = 1/2t \sim t$$

$$L = 50$$

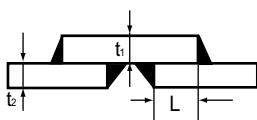
## ㉒ : Closing by butt weld



$$\theta = 40^\circ \pm 5^\circ$$

$$t_1 \geq t_2$$

## ㉓ : Closing by lapping piece



$$t_1 \geq t_2$$

$$L = 50$$

㉔ : In case where it is difficult from structural point of view to open a hole over 300, it is to be welded carefully by low hydrogen electrode after preheating and to be confirmed by non-destructive testing.

## 9. SURFACE FINISH CONDITION

Section	Area	Scope of staging sockets and lifting eye piece to be removed	Remarks
9-1. Staging sockets	In tank	Not to be removed	<ul style="list-style-type: none"> <li>•Lifting eye pieces concerned with fatigue strength to be removed.</li> <li>•Method of removing               <ol style="list-style-type: none"> <li>① Parts of ruining appearance and passages to be flush to base plate.</li> <li>② Others to be done by gas cutting at the bond zone.</li> </ol> </li> </ul> <div data-bbox="938 864 1200 1033"> </div>
	In engine room	Not to be removed, except disturbance to passages or cargo handling	
	In hold	Ditto	
	Exposed parts of shell, upper deck etc.	To be removed	
9-2. Lifting eye piece	In tank	Not to be removed, except disturbance to passages or cargo handling	<p>but, the parts being especially important for strength to be soft toe.</p>
	In engine room	Ditto	
	In hold	Ditto	
	Exposed parts of shell, upper deck etc.	To be removed	

Note : The details will be prepared for each project, respectively.

Item	Details	Standard treatment	
		Area	Remarks
9-3. Welding bead for repair of notches		Non-exposed areas (Cargo hold, H.F.O & W.B.tanks, Void, etc.)	Remain welding beads
		Exposed areas	Weld and flush grind off

## 10. MARKING ON SHIP SIDE

Unit : mm

Item	Details	Standard range	Tolerance limits	Remarks
marking on ship side	Draft marks	$\pm 1.0$	$\pm 2.0$	To be checked at marking condition
	Freeboard marks	$\pm 0.5$	$\pm 0.5$	

## II . PAINTING PART

### 1. PRIMARY SURFACE PREPARATION AND PRE-PRIMING

Item	Details	Standard treatment	
		Grade	Thickness of priming
1-1. Steel plates and sections	Hull structural members of steel thickness 6mm and above	Shot and grit blasting ISO 8501-1-Sa 2½	An average $15 \pm 5 \mu\text{m}$ dry film thickness of inorganic zinc shop primer.
1-2. Outfitting	Pipes, Supports, Seats, etc	Pickling or Power tooling ISO 8501-1- St 2	No pre-priming shall be applied basically

### 2. SECONDARY SURFACE PREPARATION

#### 2-1. Surface preparation grade

Grade	Standard
Sa 2½	It shall comply with ISO standard and then correspond in appearance to the photographs designated Sa 2½.
T/UP Sa 2½	Damaged shop primed area and welding line to be treated to Sa 2½. Intact shop primed area shall remain as it is. Any remaining traces of contamination shall show only as slight stains in the form of spots or stripes.
Sa 1	It shall comply with ISO standard and then correspond in appearance to the photographs designated Sa 1.
Pt3	It shall comply with JSRA standard and then correspond in appearance to the photographs designated Pt3.
Pt2	It shall comply with JSRA standard and then correspond in appearance to the photographs designated Pt2.

Abbr.) T/UP : Partial treatment for damaged and rusted spot

## 2-2. Standard grade of surface cleaning

Items	Standard
Oil and fat	The remaining traces may be visible
Zinc salt	Irremovable by soft hand touch
Fume by welding or gas cutting	Irremovable by soft hand touch
Chalk marks	To be removed, but the traces removed may be visible
Talc chalk marks	Not to be removed
Marking paints	Marking paints compatible with subsequent coats should not be removed
Other foreign matters	The remaining traces may be visible

## 2-3. Damaged parts after pre-erection and erection

Details	Standard	
	Grade	Remarks
Rusted, burnt and joint area	Power tooling - Pt2 or Pt3 (JSRA)	In general, surrounding areas to be feathered to ensure adhesion between coats as shown in Fig.
Mechanically damaged area	Light disc-feathering or hand sand-papering	
Intact coating immediately adjacent areas for repair	Feathered with disc or sand -papering.	

Fig.

The diagram illustrates the required feathering for different types of surface damage. It shows a cross-section of a steel substrate with two coats of paint (1st coat and 2nd coat). A central area represents the 'welding joint line or burnt damage'. On either side of this central area, the diagram shows how the paint coats should be feathered into the surrounding steel. The 'light disk feathering' is indicated by the gradual transition of the paint layers from the damaged area to the intact surface.






## 2-4. Preparation of edges and treatment of welding spatter

### 1) Sharp edge

One pass grinding (1C) shall be applied at hull fabrication shop for Water Ballast Tank, Fresh Water Tank and exposed area.

For other dry space sharp edge shall not be treated to 1C.

### 2) welding spatters

Unstable spatter		Spatters shall be removed by hand & power tools.
Stable but sharp angle		Sharp angle spatter shall be ground off until the angle becomes obtuse.
Stable and obtuse		Spatter shall be left.

### 3) Rolled edges

Rolled edges of section shall not be smoothed by mechanical tools.

### 3. PAINTING

Items	Standard	Remarks
Painting appliance	Airless spray, roller and brush	Airless spray to be adopted mainly, but roller and brush also can be used where they are more suitable
Stripe coat	<p>All kind of hole and free edge</p> <ul style="list-style-type: none"> <li>- to be coated with roller or brush after main coat</li> </ul>	The stripe coating for various tank such as Water Ballast Tank etc shall be applied in accordance with the paint specification.
	<p>For manual welding or irregular welding line of wet space one time stripe coat shall be applied with roller or brush after or before 2nd coat as below</p> <ul style="list-style-type: none"> <li>- Water tight boundary and around frame - all manual welds to be striped</li> <li>- Other weld bead - rough bead(which cannot be painted properly with airless spray) only to be striped.</li> </ul>	
	<p>Behind angle</p> <ul style="list-style-type: none"> <li>- stripe coat shall be applied with roller after or before 2nd coat</li> </ul>	In case of low D.F.T touch up shall be applied.

## 4. AMBIENT CONDITION

Items	Standard	Remarks
Ambient condition	Surface temperature - No limitation	In all cases, Limitation on max. or min. surface temperature in the manufacturer's instructions shall be followed (Depend on products)
	Relative humidity - Below 85%	
	Dew point - steel temperature should be 3°C above dew point	Surface must be free from condensation

## 5. D.F.T MEASUREMENT

Details	Standard
Dry film thickness	Total Dry Film Thickness specified in the painting specification shall be attained at least 90% of measuring point, and the film thickness on the remaining 10% measuring point shall not be less than 90% of this specified film thickness.
Measuring point	In general, the five (5) separate spot measurements shall be made over every 10m <sup>2</sup> in tanks and for each 20m <sup>2</sup> in other spaces. The average of five (5) separate spot measurements must be within the specified thickness, while single spot measurements are permitted to be 90% of the specified thickness.
Non-measuring areas	No measurement of Dry Film Thickness shall be made on; 1. Machinery and the like and on non-corrosive materials. 2. Outfittings and pipes with nominal diameter of 250mm and below 3. Pipe supports, machinery seats and small fittings 4. Areas within 50mm from edges of painted steel members, welding beads.

## 6. TIME FOR D.F.T MEASUREMENT

The measurement of Dry Film Thickness shall be carried out in accordance with the following table.

〈Standard for measuring of Dry Film Thickness〉

Kind of Paint Time Area		Epoxy		Alkyd or other conventional paint
		After A/C paint	After final coating	After A/C paint
Bottom shell		0	0	-
Side shell		0	0	-
Exposed part		0	-	-
Various tank		-	0	-
Accommodation	out	0	-	-
E/ casing	in	-	-	*0
E/ Room, Void, Cofferdam and Dry space		-	-	*0

\* In E/R, void, cofferdam and dry space, D.F.T will not be checked always.

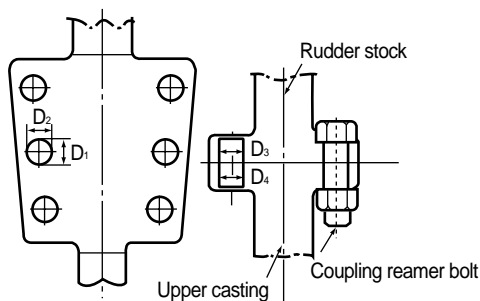
Only painting condition will be inspected to ensure no bare steel or holiday.

### Ⅲ . OUTFITTING PART

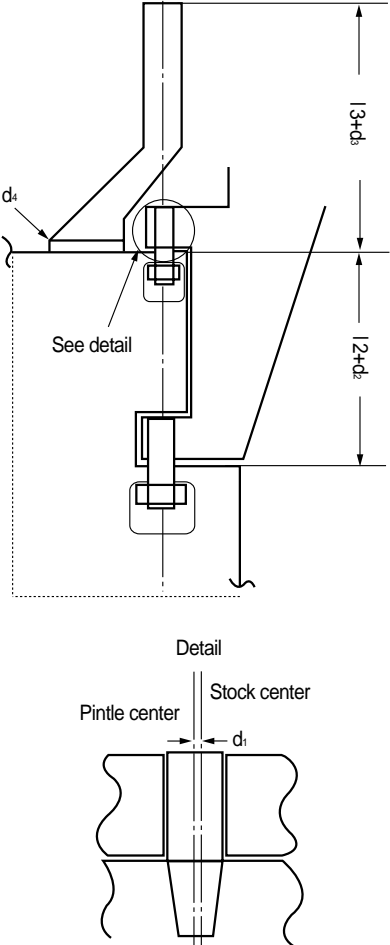
#### 1. MAIN MACHINERY

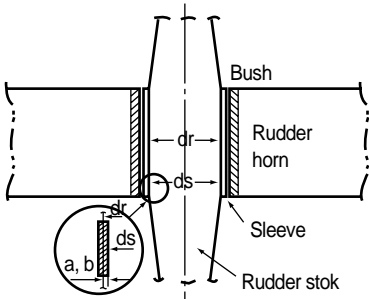
Unit : mm

Section	Item	Standard range	Tolerance limits
1-1. Rudder	1-1-1. Centering a. Diameter of piano wire b. Tension of piano wire c. Tolerance between shaft & rudder centers  1-1-2. Boring a. Eccentricity of rudder horn (upper, lower gudgeon) after boring	0.4~0.7 50kg $\leq 8$  $\leq 0.05$	$\pm 5 \text{ kg}$
1-2. Steering system	1-2-1. Rudder upper casting & rudder stock a. Reamer bolt size & hole size a-1 : Roundness   $D_1-D_2$   a-2 : Difference   $D_3-D_4$   (Top diameter to bottom diameter) a-3 : Interference $D=D_b-D_h$ $D_b$ : Bolt diameter $D_h$ : Hole diameter	$\leq 0.01$ $\leq 0.02$  $0.005 \leq D \leq 0.015$	

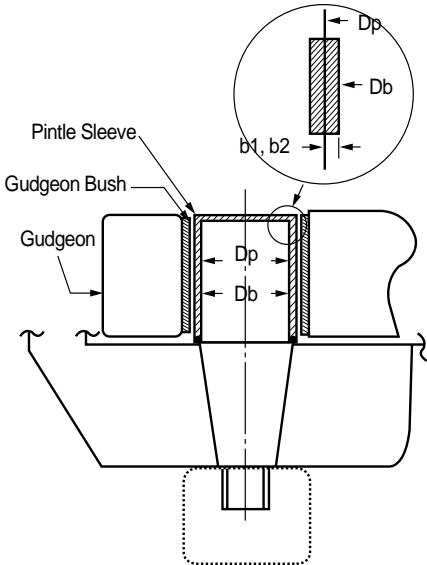
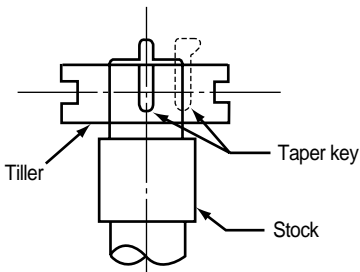


Unit : mm

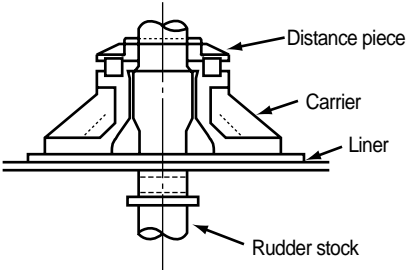
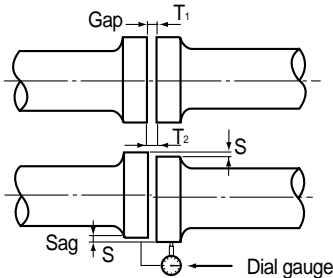
Section	Item	Standard range	Tolerance limits
1-2. Steering system	<p>1-2-2. Jointing</p> <p>a. Contact area ratio(between rudder and stock)</p> <p>b. Over set(pintle center to stock center)</p> <p>c. Length of rudder stock</p> <p>d. Length of rudder</p> <p>e. Total length of rudder with stock</p> <p>f. Gap(stock palm and rudder after tightening of reamer bolt)</p> 	<p><math>\geq 70\%</math></p> <p><math>d_1 \leq 0.3</math></p> <p><math>d_3 = \pm 3</math></p> <p><math>d_2 = \pm 5</math></p> <p><math>\pm 5</math></p> <p><math>d_4 \leq 0.04</math></p>	<p><math>\leq 0.5</math></p> <p>Clearance within 10mm depth can be allowed.</p>

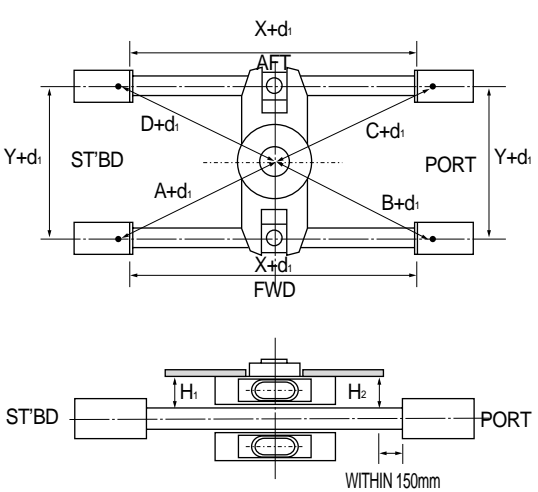
Section	Item	Standard range	Tolerance limits
1-2. Steering system	<p>1-2-3. Sleeve on rudder stock</p> <p>a. “SUS” sleeve(interference)  <math>dr-ds=a</math></p> <p>b. “BC” sleeve(interference)  <math>dr-ds=b</math></p> <p>Where, <math>dr</math> : stock outer diameter  <math>ds</math> : sleeve inner diameter</p> 	$a = \frac{(5 \sim 10)dr}{10,000}$ $b = \frac{(10 \sim 20)dr}{10,000}$	
	<p>1-2-4. Pintle</p> <p>a. Contact area ratio on taper cone part  <math>\geq 70\%</math></p> <p>b. Interference between pintle and sleeve</p> <p><math>b_1</math> : “SUS” sleeve <math>D_p - D_b</math>  <math display="block">b_1 = \frac{(5 \sim 10)D_p}{10,000}</math></p> <p><math>b_2</math> : “BC” sleeve <math>D_p - D_b</math>  <math display="block">b_2 = \frac{(10 \sim 20)D_p}{10,000}</math></p> <p>Where, <math>D_b</math> : Sleeve inner diameter  <math>D_p</math> : Pintle outer diameter</p>		

Unit : mm

Section	Item	Standard range	Tolerance limits
1-2. Steering system	<p>1-2-4. Pintle DWG.</p>  <p>1-2-5. Gudgeon bush(interference)</p> <p>a. "BC", "SUS" sleeve Dh-Dg</p> <p>b. Lignumvitae or phenol resin Dh-Dg</p> <p>Dh : Bush outer diameter</p> <p>Dg : Gudgeon inner diameter</p> <p>1-2-6. Rudder stock and rudder tiller</p> <p>a. Clearance of taper key</p> 	<p>0.05*</p> <p>0.05*</p> <p>0.005~0.015</p>	<p>* To be in accordance with maker's instruction.</p>

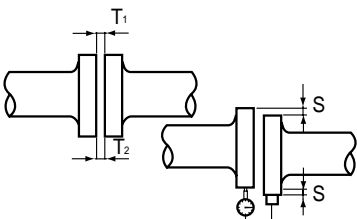


Section	Item	Standard range	Tolerance limits
1-2. Steering system	<p>1-2-7. Installation of rudder carrier and stuffing box</p> <p>a. Liner contact area(ratio)</p> <p>b. Clearance between carrier and liner after bolt tightening</p>  <p>1-2-8. Ram cylinder type(steering gear)</p> <p>a. Reamer bolt fitting Db-Dh Db : Bolt outer diameter Dh : Hole inner diameter</p> <p>b. Liner(top liner &amp; chock liner) Clearance after bolt tightening</p> <p>c. Ram cylinder installation horizontal level and distortion d<sub>i</sub> : Clearance of ram cylinder</p> <p>d. Coupling's alignment of hyd. oil pump</p> <ul style="list-style-type: none"> <li>• Gap(face)   T<sub>1</sub>-T<sub>2</sub>  </li> <li>• Sag(circum.) S</li> </ul> 	<p><math>\geq 60\%</math></p> <p><math>\leq 0.05</math></p> <p><math>0.005 \leq D \leq 0.015</math></p> <p><math>&lt; 0.06</math></p> <p><math>\leq 0.07d_i</math></p> <p><math>\leq 0.05</math></p> <p><math>\leq 0.05</math></p>	<p>Maker's standard</p>

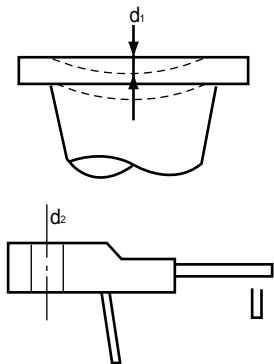
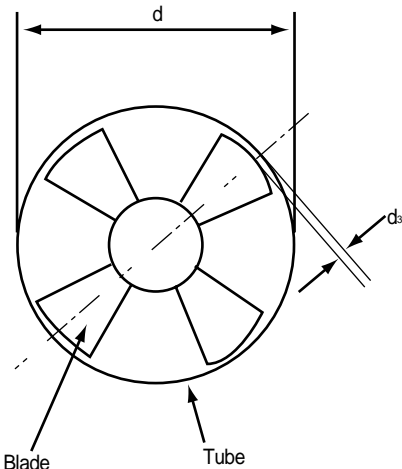
Section	Item	Standard range	Tolerance limits
1-2. Steering system	<p>1-2-9. Rotary vane type(steering gear)</p> <p>a. Taper part of rudder stock and steering gear boss</p> <ul style="list-style-type: none"> <li>• Ratio of contact area</li> </ul> <p>b. Travel length of force fitting</p> <p>c. Coupling's alignment(solid type) of hyd. oil pump</p> <ul style="list-style-type: none"> <li>• Gap(face)   T1-T2  </li> <li>• Sag(circum) S</li> </ul> <p>1-2-10. Alignment of steering gear</p>  <p>1-2-11. Main engine installation</p> <p>1. Contact ratio</p> <ul style="list-style-type: none"> <li>Main engine chock liner</li> <li>Bearing chock liner</li> </ul> <p>2. Clearance between liner and base (After holding down bolt tightening)</p>	<p><math>\geq 70\%</math></p> <p>*</p> <p><math>\leq 0.05</math></p> <p><math>\leq 0.05</math></p> <p><math>d_1 \leq 1</math></p> <p><math> H_1-H_2  \leq 0.08</math></p> <p><math>\geq 70\%</math></p> <p><math>\geq 60\%</math></p> <p><math>\leq 0.04</math></p>	<p>* According to maker's recommendation</p> <p>Maker's standard</p> <p><math>d_1 \leq 2</math></p> <p><math> H_1-H_2  \leq 0.15</math></p> <p><math>\geq 60\%</math></p> <p><math>\geq 50\%</math></p>

## 2. AUXILIARY MACHINERY

Unit : mm

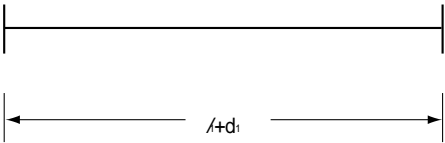
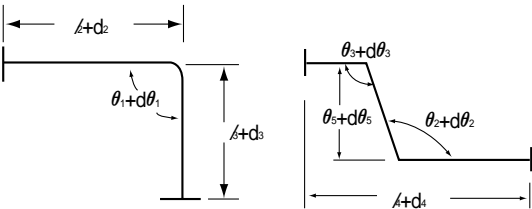
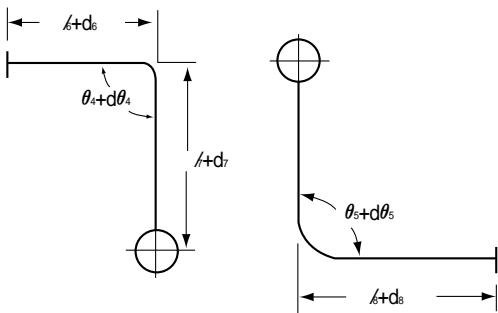
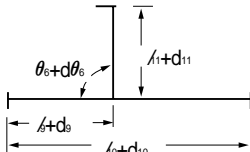
Section	Item	Standard range	Tolerance limits
2-1. Aux. machinery	<p>2-1-1. Auxiliary machinery(E/R.DK)</p> <p>Installation of aux. machinery shall be carried out in accordance with the following three grades.</p> <p>Feeler guage measurement between seat &amp; machine shall be carried out after tightening of holding down bolts.</p> <p>(1) Grade "A" : Diesel generator, Turbo generator, Shaft generator, Inter shaft bearing, Windlass.</p> <p>(2) Grade "B" : Fresh water pump, Cooling water pump, Fire pump, Fuel oil pump, Ballast pump, Lub oil pump, Bilge &amp; General service pump, Emergency diesel &amp; fire pump, Emergency diesel generator, Air compressor, Cargo pump &amp; motor &amp; turbine.</p> <p>(3) Grade "C" : Other machinery which are not listed "Grade A" and "Grade B".</p> <p>- Tightness of holding down bolts shall be checked by hammering after installation completed.</p>	<p><math>\leq 0.04</math></p> <p><math>\leq 0.05</math></p> <p>-</p>	<p>The feeler gauge of standard thickness should not be inserted more than 10mm</p> <p>-</p>
2-2. General aux. pumps	<p>2-2-1. Coupling alignment of aux. pumps (solid type)</p> 		

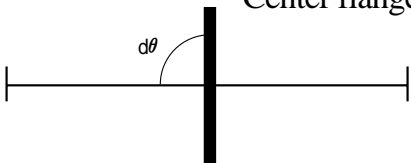
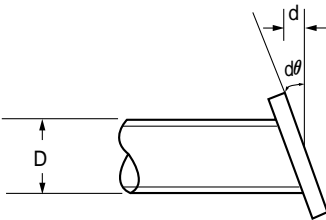
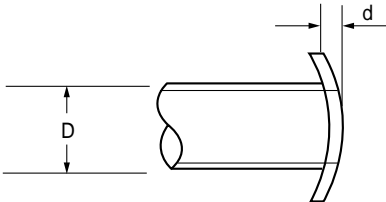

Unit : mm

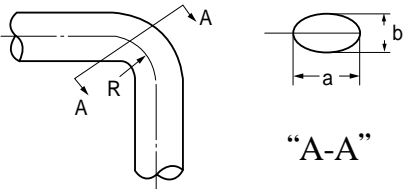

Section	Item	Standard range	Tolerance limits
2-3. Bow thruster (If any discrepancy is found between the SSQS and maker's standard, the maker's standard shall prevail.)	a. Gap(face)      $T_1 - T_2$	$\pm 0.05$	Maker's standard
	b. Sag(circum)    S	$\pm 0.05$	
	2-3-1. Installation of shaft		
	a. Plane of flange $d_1$ b. Difference of bolt hole on flange $d_2$ 	$d_1 \leq 0.4$ $d_2 \leq 0.6$	- -
	2-3-2. Clearance between tube and blade		
		$d_3 \geq \frac{d}{600}$	-


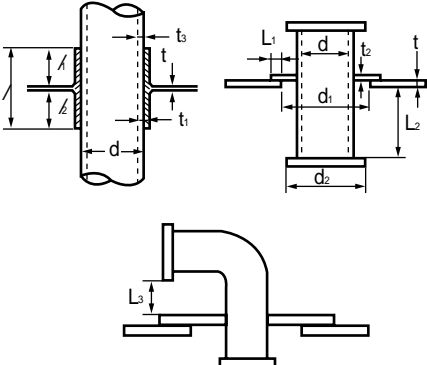
### 3. PIPING

Unit : mm

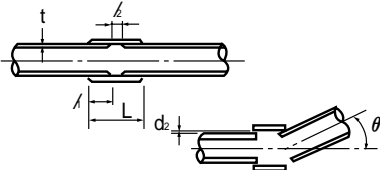
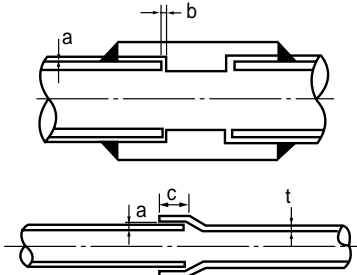


Section	Item	Standard range	Remarks
3-1. Pipe fabrication	<p>3-1-1. Cutting, bending &amp; etc.</p> <p>a. Straight pipe</p>  <p>b. Bending pipe</p>  <p>(Two directional bending)</p>  <p>(Three directional bending)</p> <p>c. Branch pipe</p> 	<p><math>d_1 = \pm 2</math></p> <p><math>d_2 = \pm 2</math>  <math>d_3 = \pm 2</math>  <math>d_4 = \pm 2</math>  <math>d_5 = \pm 2</math></p> <p><math>d\theta_1 = \pm 1^\circ</math>  <math>d\theta_2 = \pm 1^\circ</math>  <math>d\theta_3 = \pm 1^\circ</math></p> <p><math> \theta_2 - \theta_3  \leq 2^\circ</math></p> <p><math>d_6 = \pm 2</math>  <math>d_7 = \pm 2</math>  <math>d_8 = \pm 2</math>  <math>d\theta_4 = \pm 1^\circ</math>  <math>d\theta_5 = \pm 1^\circ</math></p> <p><math>d_9 = \pm 2</math>  <math>d_{10} = \pm 2</math>  <math>d_{11} = \pm 2</math>  <math>d\theta_6 = \pm 1^\circ</math></p>	<p>1. <math>L, L \dots</math> Indicated length on the drawing</p> <p>2. <math>\theta_1, \theta_2 \dots</math> Indicated angle on the drawing</p> <p>3. <math>d_1, d_2 \dots</math> Tolerance between Indicated length on the drawing and actually made one</p> <p>4. <math>d\theta_1, d\theta_2 \dots</math> Tolerance between angle on the drawing and actually made one</p>

Section	Item	Standard range	Remarks
3-1. Pipe fabrication	d. Penetration piece		
	 <p>Center flange</p>	$d\theta \leq \pm 0.5^\circ$	
	3-1-2. Fitting of flange		
	a. Angle of flange to pipe		
		$d\theta \leq \pm 0.5^\circ$	$-d \leq \max. 2$ D : Pipe normal diameter
	b. Bending of flange		
		a) $d \leq 1.5$ when $D \geq 500$ b) $d \leq 1.0$ when $200 \leq D < 500$ c) $d \leq 0.5$ when $D < 200$	d: Bend dimension
	c. Distance between flange and bending area		
		$L \geq t$ $R \geq 2D$	
	Note : Elbow piece can be connected to the flange directly		



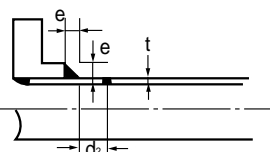
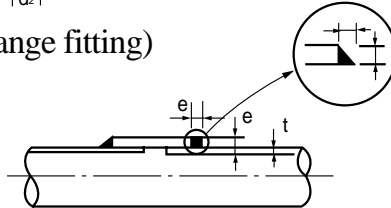
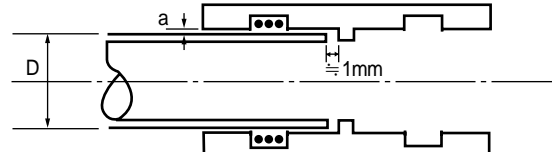
Section	Item	Standard range																								
3-1. Pipe fabrication	<p>3-1-3. Transformation by bending</p> <p>a. Ellipticity (E)</p>  <p style="text-align: center;">“A-A”</p> $* E = \frac{ a - b }{D} \times 100\%$ $* B = \frac{t - t_1}{t} \times 100\%$ <p>where D : Outer diameter of pipe  B : Thickness reduction ratio  t : Original pipe thickness  t<sub>1</sub> : Thickness after bending  R : Bending radius  a : Large diameter  b : Small diameter</p> <p>b. Wrinkle</p>  <p>where,  h : Wrinkle height  D : Outer diameter  of pipe</p>	<p><math>E \leq 10\%</math></p> <p>* In accordance with class rule requirement</p> <p>B : As below</p> <p>Steel pipe bending</p> <table border="1"> <thead> <tr> <th>Radius</th><th>Hot bend</th><th>Cold bend</th></tr> </thead> <tbody> <tr> <td><math>R \leq 2D</math></td><td><math>B \leq 15\%</math></td><td><math>B \leq 25\%</math></td></tr> <tr> <td><math>2D &lt; R \leq 3D</math></td><td><math>B \leq 10\%</math></td><td><math>B \leq 20\%</math></td></tr> <tr> <td><math>R &gt; 3D</math></td><td><math>B \leq 5\%</math></td><td><math>B \leq 15\%</math></td></tr> </tbody> </table> <p>Copper pipe bending</p> <table border="1"> <thead> <tr> <th>Radius</th><th>Hot bend</th><th>Cold bend</th></tr> </thead> <tbody> <tr> <td><math>R \leq 2D</math></td><td><math>B \leq 20\%</math></td><td><math>B \leq 30\%</math></td></tr> <tr> <td><math>2D &lt; R \leq 3D</math></td><td><math>B \leq 15\%</math></td><td><math>B \leq 20\%</math></td></tr> <tr> <td><math>R &gt; 3D</math></td><td><math>B \leq 10\%</math></td><td><math>B \leq 15\%</math></td></tr> </tbody> </table> <p><math>h &lt; 2</math></p>	Radius	Hot bend	Cold bend	$R \leq 2D$	$B \leq 15\%$	$B \leq 25\%$	$2D < R \leq 3D$	$B \leq 10\%$	$B \leq 20\%$	$R > 3D$	$B \leq 5\%$	$B \leq 15\%$	Radius	Hot bend	Cold bend	$R \leq 2D$	$B \leq 20\%$	$B \leq 30\%$	$2D < R \leq 3D$	$B \leq 15\%$	$B \leq 20\%$	$R > 3D$	$B \leq 10\%$	$B \leq 15\%$
Radius	Hot bend	Cold bend																								
$R \leq 2D$	$B \leq 15\%$	$B \leq 25\%$																								
$2D < R \leq 3D$	$B \leq 10\%$	$B \leq 20\%$																								
$R > 3D$	$B \leq 5\%$	$B \leq 15\%$																								
Radius	Hot bend	Cold bend																								
$R \leq 2D$	$B \leq 20\%$	$B \leq 30\%$																								
$2D < R \leq 3D$	$B \leq 15\%$	$B \leq 20\%$																								
$R > 3D$	$B \leq 10\%$	$B \leq 15\%$																								

Section	Item	Standard range	Remarks
3-1. Pipe fabrication	3-1-4. Distance between the flange and the branch pipes 	$A \geq 30$ $A/2 \geq 30$	$A/2$ : Distance between flange face and the pipe surface can be reduced in unavoidable situation.
	3-1-5. Fitting of penetration piece 	$\neq 100$ when $d \leq 65$ $\neq 150$ when $d \geq 80$ $\neq 200$ when $d \geq 550$ $A, A/2 \geq 15$  $t_2 = 12$ when $t \leq 12$ $t_2 = 15$ when $12 < t < 15$ $t_2 = 20$ when $t \geq 15$ $t_1 \geq t_3$ $L_1 = 30 \pm 5$ when $d \leq 100$ $L_1 = 40 \pm 5$ when $125 \leq d \leq 500$ $L_1 = 50 \pm 5$ when $d \geq 550$ $d_1 = d_2 + 10$ $L_2 \geq 50$ $L_3 \geq 25$	d: Pipe nominal diameter

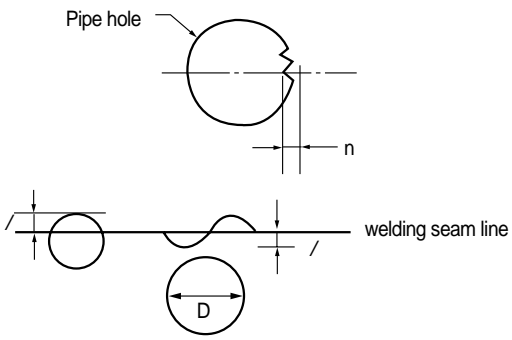
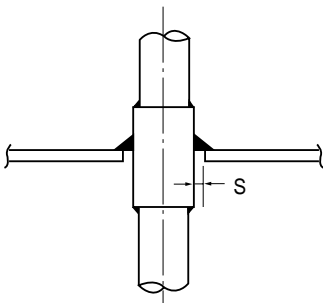

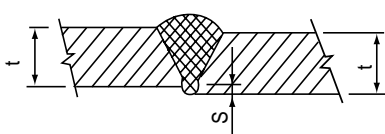


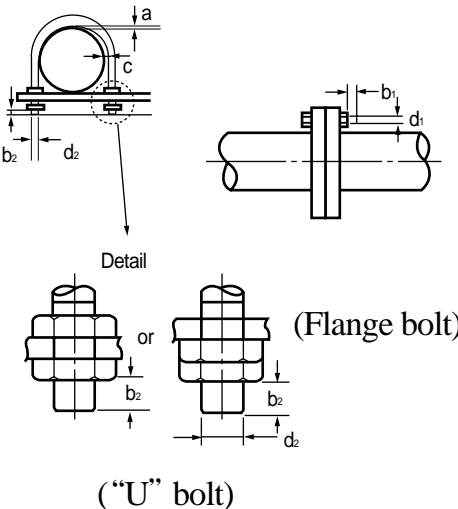
Section	Item	Standard range	Remarks
3-1. Pipe fabrication	3-1-6. Sleeve welding Joint	$L \geq 50$ $L \geq 9.5$ when $D \leq 65$ $L \geq 25$ when $D \geq 80$ $L \geq 2$ $d_2 \leq 2.0$ $\theta < 3^\circ$	Grade of pipes will be decided according to the concerned class rules.
			
	3-1-7. Socket welding Joint	$a \leq 0.8$ $b \leq 1.5$	
			
	3-1-8. Solder brazing Joint (Silver brazing)	$0.05 \leq a \leq 0.15$	
	3-1-9. Welding		
	a. Weld groove	$a = 3 \pm 0.5$ $b = 1.6 \pm 0.8$ $\theta_1 = 60^\circ \pm 5^\circ$	Grade of pipes will be decided according to the concerned class rules.
	 <p>(Grade I pipe)</p>		
	 <p>(Grade II , III &amp; others)</p>	$t < 4.8 : a < 2.0$ $t \geq 4.8 : a = 1 \sim 4$ $a_1 = 0 \sim 2$ $\theta \geq 30^\circ$	

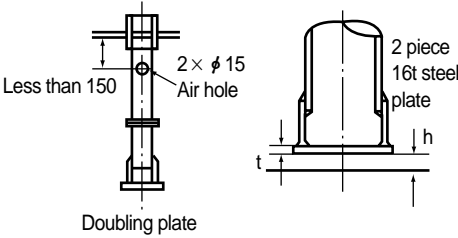


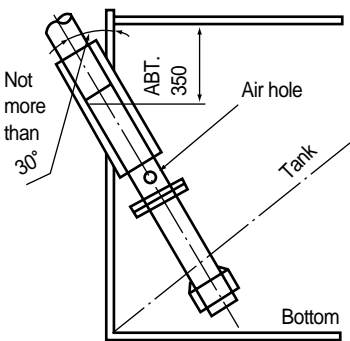
Unit : mm

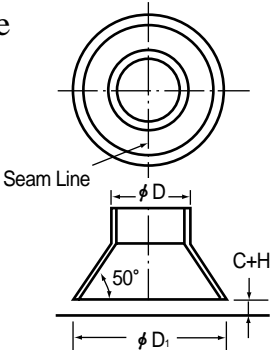
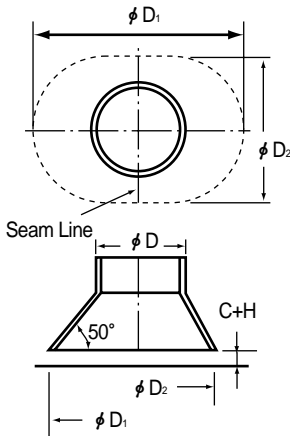

Section	Item	Standard range	Remarks
3-1. Pipe fabrication	b. Back bead of weld	Class I, II pipe	
	 (Class I, II)	pipe thickness (t, mm)	back height (d, mm)
		$t \leq 6$	$d \leq 1.5$
		$6 > t$	$d \leq 3.0$
		Class III pipe & others $d_1 \leq 0.5$	
	c. Undercut of weld	$d \leq 0.5$	
			
	d. Leg length of weld	$e \geq t$ $d_2 \geq 5$	In accordance with design practice
	 (Flange fitting)		
	 (Sleeve jointing)	$e \geq t$	In accordance with design practice
	3-1-10. Al-brass brazing joint	when $D=10 \sim 40$ $0.05 \leq a \leq 0.08$ max. $a=0.15$ when $D=50 \sim 100$ $0.05 \leq a \leq 0.1$	
			

Unit : mm

Section	Item	Standard range	Remarks												
3-2. Pipe fitting	3-2-1. Pipe hole cutting & penetration	<p>Holes on the main structure <math>n \leq 0.8</math></p> <p>Holes not on the main structure <math>n \leq 1.5</math> <math>\neq 0.1D</math> (min. 50)</p>	Only one side welding to be applied except upp. Deck, Tank BHD & Fore/ Aft BHD.												
	a. Hole cutting finishing														
	b. Pipe penetration			$s \leq 5$											
	3-2-2. Alignment														
	a. flange			$a \leq 2$ $c-b \leq 2$											
	b. pipe and Fittings			<table><tr><th>pipe indiameter (D, mm)</th><th>pipe thickness (t, mm)</th><th>internal misalignment (S, mm)</th></tr><tr><td><math>D &lt; 150</math></td><td><math>t \leq 6</math></td><td>Smaller value of <math>S \leq 1</math> or <math>t/4</math></td></tr><tr><td><math>150 \leq D &lt; 300</math></td><td><math>t \leq 9.5</math></td><td>Smaller value of <math>S \leq 1.5</math> or <math>t/4</math></td></tr><tr><td colspan="2"><math>300 \leq D</math> or <math>9.5 &lt; t</math></td><td>Smaller value of <math>S \leq 2.0</math> or <math>t/4</math></td></tr></table>	pipe indiameter (D, mm)	pipe thickness (t, mm)	internal misalignment (S, mm)	$D < 150$	$t \leq 6$	Smaller value of $S \leq 1$ or $t/4$	$150 \leq D < 300$	$t \leq 9.5$	Smaller value of $S \leq 1.5$ or $t/4$	$300 \leq D$ or $9.5 < t$	
pipe indiameter (D, mm)	pipe thickness (t, mm)	internal misalignment (S, mm)													
$D < 150$	$t \leq 6$	Smaller value of $S \leq 1$ or $t/4$													
$150 \leq D < 300$	$t \leq 9.5$	Smaller value of $S \leq 1.5$ or $t/4$													
$300 \leq D$ or $9.5 < t$		Smaller value of $S \leq 2.0$ or $t/4$													

Section	Item	Standard range	Remarks																																												
3-2. Pipe fitting	<p>3-2-3. Bolting</p>  <p>3-2-4. Distance between bands of supports</p> <table border="1"> <thead> <tr> <th>Pipe nominal dia:A</th><th>Max. distance</th><th>Pipe nominal dia:A</th><th>Max. distance</th></tr> </thead> <tbody> <tr><td>10</td><td>1.4m</td><td>125</td><td>4.5m</td></tr> <tr><td>15</td><td>1.6m</td><td>150</td><td>5.0m</td></tr> <tr><td>20</td><td>1.8m</td><td>200</td><td>5.0m</td></tr> <tr><td>25</td><td>2.1m</td><td>250</td><td>5.5m</td></tr> <tr><td>32</td><td>2.4m</td><td>300</td><td>6.0m</td></tr> <tr><td>40</td><td>2.6m</td><td>350</td><td>6.0m</td></tr> <tr><td>50</td><td>2.8m</td><td>400</td><td>6.0m</td></tr> <tr><td>65</td><td>3.2m</td><td>500</td><td>7.0m</td></tr> <tr><td>80</td><td>3.5m</td><td>600</td><td>7.0m</td></tr> <tr><td>100</td><td>4.0m</td><td>700</td><td>7.0m</td></tr> </tbody> </table> <p>Above standard distance will be adopted as working guideline that is, the distance can be increased depending on the actual installation condition.</p>	Pipe nominal dia:A	Max. distance	Pipe nominal dia:A	Max. distance	10	1.4m	125	4.5m	15	1.6m	150	5.0m	20	1.8m	200	5.0m	25	2.1m	250	5.5m	32	2.4m	300	6.0m	40	2.6m	350	6.0m	50	2.8m	400	6.0m	65	3.2m	500	7.0m	80	3.5m	600	7.0m	100	4.0m	700	7.0m	<p>* <math>b_1 \leq \frac{d_1}{2}</math></p> <p>* <math>b_2 \leq \frac{d_2}{2}</math></p> <p><math>a \leq 2</math></p> <p><math>0 \leq c \leq 2</math></p>	* Marked standard will be adopted as working guideline
Pipe nominal dia:A	Max. distance	Pipe nominal dia:A	Max. distance																																												
10	1.4m	125	4.5m																																												
15	1.6m	150	5.0m																																												
20	1.8m	200	5.0m																																												
25	2.1m	250	5.5m																																												
32	2.4m	300	6.0m																																												
40	2.6m	350	6.0m																																												
50	2.8m	400	6.0m																																												
65	3.2m	500	7.0m																																												
80	3.5m	600	7.0m																																												
100	4.0m	700	7.0m																																												



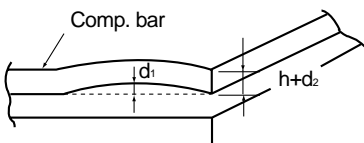
Section	Item	Standard range	Remarks
3-2. Pipe fitting	<p>3-2-5. Sounding pipe</p> <p>a. Straight type</p>  <p>b. Special type</p> <p>b-1. Box type</p>  <p>b-2. Elbow sounding</p>  <p>b-3. Bow sounding type</p> 	<p><math>t=15</math> <math>h=20 \pm 5</math></p>	

Section	Item	Standard range	Remarks
3-2. Pipe fitting	3-2-6. Suction bellmouth		
	A-type 	$H = \pm 10$ $H = \pm 5$	Main line Stripping line
	B-type 	$H = \pm 10$ $H = \pm 5$	Main line Stripping line
	C-type 	$H = \pm 5$	



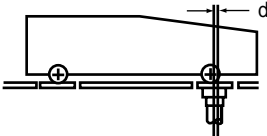
Section	Item	Standard range	Remarks																																											
3-2. Pipe fitting	a. A-type	$H = \pm 10$ $H = \pm 5$	Main line Stripping line																																											
	<table><tr><th rowspan="2">Nominal dia</th><th colspan="2">Bellmouth Dimension</th><th rowspan="2">C</th></tr><tr><th>D</th><th>D<sub>1</sub></th></tr><tr><td>80</td><td>89.1</td><td>200</td><td>15</td></tr><tr><td>100</td><td>114.3</td><td>275</td><td>20</td></tr><tr><td>125</td><td>139.8</td><td>400</td><td>20</td></tr><tr><td>150</td><td>165.2</td><td>450</td><td>25</td></tr><tr><td>200</td><td>216.3</td><td>550</td><td>35</td></tr></table>			Nominal dia	Bellmouth Dimension		C	D	D <sub>1</sub>	80	89.1	200	15	100	114.3	275	20	125	139.8	400	20	150	165.2	450	25	200	216.3	550	35																	
	Nominal dia				Bellmouth Dimension			C																																						
				D	D <sub>1</sub>																																									
	80			89.1	200	15																																								
	100			114.3	275	20																																								
	125			139.8	400	20																																								
	150	165.2	450	25																																										
	200	216.3	550	35																																										
	b. B-type	$H = \pm 10$ $H = \pm 5$	Main line Stripping line																																											
	<table><tr><th rowspan="2">Nominal dia</th><th colspan="3">Bellmouth Dimension</th><th rowspan="2">C</th></tr><tr><th>D</th><th>D<sub>1</sub></th><th>D<sub>2</sub></th></tr><tr><td>250</td><td>276.4</td><td>675</td><td>400</td><td>50</td></tr><tr><td>300</td><td>318.5</td><td>860</td><td>550</td><td>50</td></tr><tr><td>350</td><td>355.6</td><td>865</td><td>550</td><td>80</td></tr><tr><td>400</td><td>406.4</td><td>1000</td><td>600</td><td>80</td></tr><tr><td>450</td><td>457.2</td><td>1170</td><td>600</td><td>100</td></tr><tr><td>500</td><td>508.6</td><td>1240</td><td>750</td><td>100</td></tr><tr><td>550</td><td>558.3</td><td>1410</td><td>750</td><td>120</td></tr></table>			Nominal dia	Bellmouth Dimension			C	D	D <sub>1</sub>	D <sub>2</sub>	250	276.4	675	400	50	300	318.5	860	550	50	350	355.6	865	550	80	400	406.4	1000	600	80	450	457.2	1170	600	100	500	508.6	1240	750	100	550	558.3	1410	750	120
	Nominal dia				Bellmouth Dimension				C																																					
				D	D <sub>1</sub>	D <sub>2</sub>																																								
	250			276.4	675	400	50																																							
	300			318.5	860	550	50																																							
	350			355.6	865	550	80																																							
	400			406.4	1000	600	80																																							
	450	457.2	1170	600	100																																									
	500	508.6	1240	750	100																																									
	550	558.3	1410	750	120																																									
	c. C-type	$H = \pm 5$																																												
	<table><tr><th rowspan="2">Nominal dia</th><th>Bellmouth Dimension</th><th rowspan="2">C</th></tr><tr><th>D × D<sub>1</sub></th></tr><tr><td>40</td><td>40 × 65</td><td>15</td></tr><tr><td>50</td><td>50 × 80</td><td>15</td></tr><tr><td>65</td><td>65 × 100</td><td>20</td></tr><tr><td>80</td><td>80 × 125</td><td>25</td></tr><tr><td>100</td><td>100 × 150</td><td>35</td></tr><tr><td>125</td><td>125 × 200</td><td>40</td></tr><tr><td>150</td><td>150 × 250</td><td>45</td></tr><tr><td>200</td><td>200 × 300</td><td>65</td></tr></table>			Nominal dia	Bellmouth Dimension	C	D × D <sub>1</sub>	40	40 × 65	15	50	50 × 80	15	65	65 × 100	20	80	80 × 125	25	100	100 × 150	35	125	125 × 200	40	150	150 × 250	45	200	200 × 300	65															
	Nominal dia				Bellmouth Dimension		C																																							
				D × D <sub>1</sub>																																										
	40			40 × 65	15																																									
50	50 × 80			15																																										
65	65 × 100			20																																										
80	80 × 125			25																																										
100	100 × 150			35																																										
125	125 × 200	40																																												
150	150 × 250	45																																												
200	200 × 300	65																																												


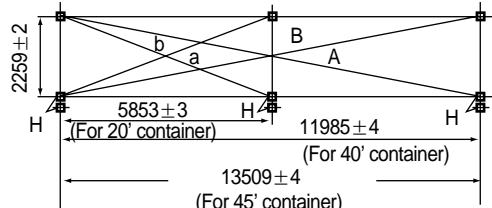

## 4. SHEET METAL OUTFITTING

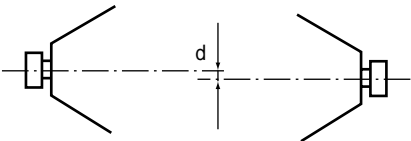
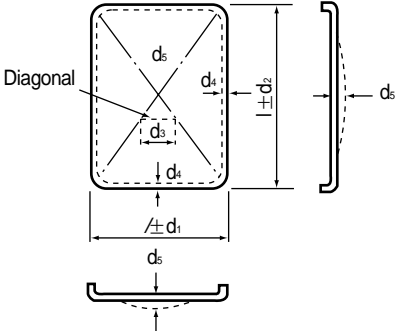
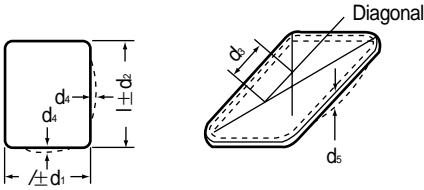
Unit : mm

Section	Item	Standard range	Remarks	
4-1. Hatch cover	4-1-1. Hatch cover			
	<div></div> <div>a. Length deviation <math>d_1</math></div> <div>b. Width deviation <math>d_2</math></div> <div>c. Height deviation <math>d_3</math></div> <div>d. Diagonal deviation <math> L_1-L_2 </math></div>	$d_1, d_2 \pm (3+\frac{4}{10,000} L)$  $\pm 3$  $\leq 10$		
	4-1-2. Deflection	<div></div>	$\pm 4$	
	4-1-3. Fitting dimension of compression bar	<div></div>		
	a. Distance from center line $d_1$ b. Compression bar level $d_2$	$\pm 5$ $\pm 4$		



Section	Item	Standard range	Remarks
4-1. Hatch cover	4-1-4. Hatch coaming		
	 <p>1) Dimension</p> <p>a. Length deviation <math>d_1</math></p> <p>b. Width deviation <math>d_2</math></p> <p>c. Diagonal deviation <math> L_1 - L_2 </math></p>	$\pm 10$  $\pm 10$  $\leq 15$	
	2) Level of top plate deviation	$\pm 3$	
	4-1-5. Inter-connection		
	 <p>a. Alignment of top plates deviation <math>d_1</math></p>	$\leq 5$	
	4-1-6. Position of jack head		
	 <p>a. Off-set(wheel &amp; jack center line) : <math>d</math></p>	$\pm 5$	

Section	Item	Standard range	Remarks												
4-1. Hatch cover	4-1-7. Water tight structure														
	a. Packing gutter(height) deviation $d_1$	$\pm 2$													
	b. Packing gutter(width) deviation $d_2$	$\pm 1$													
															
	4-1-8. Dimension for container loading (typical for on deck)														
															
	<table><tr><th>No</th><th>Measuring point</th><th>Allowable tolerance</th></tr><tr><td>1</td><td>  a-b  </td><td><math>\leq 6</math></td></tr><tr><td>2</td><td>  A-B  </td><td><math>\leq 8</math></td></tr><tr><td>3</td><td>The level differential of sockets for a container</td><td><math>\pm 3</math></td></tr></table>	No	Measuring point	Allowable tolerance	1	a-b	$\leq 6$	2	A-B	$\leq 8$	3	The level differential of sockets for a container	$\pm 3$		
No	Measuring point	Allowable tolerance													
1	a-b	$\leq 6$													
2	A-B	$\leq 8$													
3	The level differential of sockets for a container	$\pm 3$													
	4-1-9. Gap between H/Coaming and H/Cover skirt plate(Non packing type)														
		$4 \leq d \leq 20$	Maker's recommen- dation												

Section	Item	Standard range	Remarks
4-1. Hatch cover	4-1-10. Level difference of two balanced roller 	$d \leq 5$	
4-2. Steel door	4-2-1. Water tight door body a. Tolerance of width or height $d_1, d_2$ b. Difference between diagonals $d_3$ c. Straightness of side and deviation $d_4$ d. Deflection $d_5$  4-2-2. Small type steel hatch cover a. Height deviation $d_1$ b. Width or length deviation $d_2$ c. Difference between diagonals $d_3$ d. Straightness deviation $d_4$ e. Deflection $d_5$ 	$\leq 5$ $\leq 5$ $\leq 5$ $\leq 5$  $0 \sim +10$ $\leq 5$ $\leq 5$ $\leq 5$ $\leq 5$	

PART B. SCOPE OF INSPECTION

I . HULL	61
II . HULL OUTFITTING	62
III . MACHINERY	64
IV . PIPING	69
V . ELECTRIC	70
VI . PAINTING	73

ABBREVIATION

Witnessed by

- C : Class surveyor
- O : Owner supervisor
- Q : Q.A inspector
- M : Maker supervisor

# I . HULL

No	Inspection Items		In Shop				On Board				Remarks
			C	O	Q	R	C	O	Q	R	
1	Sub-assembly block inspection including leak test				○	○					In accordance with approved inspection & Test Plan
2	Block & P.E block Inspection including leak test for hull structure below super-structure deck		○	○	○						
3	Block & P.E block Inspection for Deck house & Funnel			○	○						
4	Erection joints inspection for hull structure below super-structure deck						○	○	○		
5	Erection Joints Inspection for Deck house & Funnel						○	○	○		
6	Rudder	Construction									
		Air Test	○	○	○						
7	Air and/or tank strength test for hull tanks		○	○	○		○	○	○		In accordance with approved Tank Test Plan
8	Non-Destructive Test (NDT)					○				○	In accordance with approved NDT Plan
9	Keel Sighting before Launching								○	○	
10	Measurement of Hull Dimension						○	○	○	○	
11	Confirmation of Hull Marking	Freeboard					○		○		Marking condition
		Draft					○	○	○		
		Ship name & Funnel mark		○	○			○	○		
		BHD. Mark		○	○			○	○		
12	Bottom Survey before launching						○	○	○		
13	Inclining Experiment/Dead weight measurement						○	○	○	○	According to I/E scheme

## II . HULL OUTFITTING

Inspection Items	Maker's Shop		On Board		Remarks
	C	O	C	O	
1. Anchor & chains Verification			<input type="radio"/>	<input type="radio"/>	
2. Cargo gear & rigging arrangement					
1) Crane & davit					* If cargo gear book requested
Operation & load test	<input type="radio"/>	<input type="radio"/>	<input type="radio"/> *	<input type="radio"/>	1.0 ton S.W.L, and over
2) Small davits				<input type="radio"/>	
Operation					
3. Hatch, door, window, etc.	<input type="radio"/> *				* Class A or B side scuttle
Hose test/Chalk test			<input type="radio"/> *	<input type="radio"/>	According to load line regulation
4. Ladder					
1) Accommodation ladder					
Proof load test	<input type="radio"/>		<input type="radio"/> *		* If authority requested
Operation				<input type="radio"/>	
2) Pilot ladder					
Construction	<input type="radio"/>				
Operation			<input type="radio"/>	<input type="radio"/>	Authority for safety equipment certificate. SOLAS item
5. Life saving & fire fighting equipment					
1) Lifeboat & davit					
Load test	<input type="radio"/>	<input type="radio"/>	<input type="radio"/>	<input type="radio"/>	
Equipment check	<input type="radio"/>		<input type="radio"/>	<input type="radio"/>	
2) Other life saving equipment					
Confirmation	<input type="radio"/>		<input type="radio"/>	<input type="radio"/>	
3) Rescue boat launching test with ship speed at least 5knot			<input type="radio"/>		
4) Fire fighting system					
Confirmation & testing			<input type="radio"/>	<input type="radio"/>	
5) Fire damper & Fire stop install. with operation.			<input type="radio"/>	<input type="radio"/>	
6) E/R local fire fighting sys. testing			<input type="radio"/>	<input type="radio"/>	

Inspection Items	Maker's Shop		On Board		Remarks
	C	O	C	O	
6. Ventilation 1) Air conditioning system Volume check in cabin 2) Mechanical ventilation volume check			<input type="radio"/> * <input type="radio"/>	<input type="radio"/> <input type="radio"/>	* If crew accommodation cert. Required from CLASS.
7. Accommodation facilities 1) A-60 Insulation and draft stop. 2) Galley & laundry equipment operation			<input type="radio"/> <input type="radio"/>	<input type="radio"/> <input type="radio"/>	Cable and duct penetration shall be confirmed.
8. Deck machinery 1) No load test 2) Windlass load test 3) Auto tension system operation	<input type="radio"/>	<input type="radio"/>	<input type="radio"/> <input type="radio"/>	<input type="radio"/> <input type="radio"/>	At sea trial. If applied.
9. Others 1) Tank level gauge function 2) Draft reading gauge function 3) Loading instrument function 4) Anti heeling system function			<input type="radio"/> <input type="radio"/> <input type="radio"/>	<input type="radio"/> <input type="radio"/> <input type="radio"/>	
10. Cargo hatch cover 1) Hose test 2) Operation test			<input type="radio"/>	<input type="radio"/> <input type="radio"/>	
11. Side thruster 1) Blade gap check 2) Seal leak test				<input type="radio"/> <input type="radio"/>	

### III . MACHINERY

Inspection Items	Maker's Shop		On Board		Remarks
	C	O	C	O	
1. Shafting					
1) Light beam alignment for shafting			<input type="radio"/>	<input type="radio"/>	Case by case
2) Force fitting of stern bush			<input type="radio"/>	<input type="radio"/>	
3) Force fitting of propeller			<input type="radio"/>	<input type="radio"/>	
4) Check of stern clearance			<input type="radio"/>	<input type="radio"/>	By wear down gauge
5) Leak test of stern sealing			<input type="radio"/>	<input type="radio"/>	
6) Stern tube L.O system flushing condition				<input type="radio"/>	
7) Coupling bolt fitting				<input type="radio"/>	
8) Shaft jack-up test			<input type="radio"/>	<input type="radio"/>	
9) Inter/Propeller shaft final inspection	<input type="radio"/>				
10) Propeller shaft with Propeller contact	<input type="radio"/>				
11) Propeller final machining	<input type="radio"/>				
12) Stern boss/Rudder horn casting final	<input type="radio"/>				
2. Main engine					
1) Condition check of chock liners or fast			<input type="radio"/>	<input type="radio"/>	
2) Holding down bolt tightness check (Before & After sea trial)			*	*	* Record to be submitted.
3) Crank shaft deflection (Cold & Hot)			<input type="radio"/>	<input type="radio"/>	
4) Flushing condition of L.O system				<input type="radio"/>	
5) Safety device function test	<input type="radio"/>	<input type="radio"/>	<input type="radio"/>	<input type="radio"/>	According to the approved drawing
6) Piston alignment	<input type="radio"/>	<input type="radio"/>			
7) Mooring trial			<input type="radio"/>	<input type="radio"/>	
8) Shop test	<input type="radio"/>	<input type="radio"/>	<input type="radio"/>	<input type="radio"/>	One set only
9) Overhaul inspection	<input type="radio"/>	<input type="radio"/>	<input type="radio"/>	<input type="radio"/>	
10) Starting test			<input type="radio"/>	<input type="radio"/>	



Inspection Items	Maker's Shop		On Board		Remarks
	C	O	C	O	
3. Auxiliary boiler					* Record to be submitted.
1) Hydro test	<input type="radio"/>	<input type="radio"/>			
2) Safety device test			<input type="radio"/>	<input type="radio"/>	
3) Accumulation test			<input type="radio"/>	<input type="radio"/>	
4. Economizer					
1) Hydro test	<input type="radio"/>				
2) Safety valve setting			<input type="radio"/>	<input type="radio"/>	
5. Generator engine					
1) Crank shaft deflection(Hot condition)			<input type="radio"/> *	<input type="radio"/> *	
2) Safety device test	<input type="radio"/>	<input type="radio"/>	<input type="radio"/>	<input type="radio"/>	
3) Shop test	<input type="radio"/>	<input type="radio"/>			
4) Overhaul inspection after shop trial	<input type="radio"/>	<input type="radio"/>			
6. Air compressor & air tanks					* Record to be submitted.
1) Tank hydro test	<input type="radio"/>				
2) Safety device test	<input type="radio"/>		<input type="radio"/>	<input type="radio"/>	
3) Automatic control test				<input type="radio"/>	
5) Air charging test			<input type="radio"/>	<input type="radio"/>	
7. Cargo turbine/pump & water ballast pump					
1) Safety device test	<input type="radio"/>		<input type="radio"/>	<input type="radio"/>	
2) Capacity check			<input type="radio"/> *	<input type="radio"/>	
8. Stripping pump					
1) Operating test			<input type="radio"/>	<input type="radio"/>	
9. Tank cleaning system (machine, heater, pump) Operating test				<input type="radio"/>	
10. ODME Function test			<input type="radio"/>	<input type="radio"/>	
11. Steering gear					
1) Pipe piece/Actuator hydro test	<input type="radio"/>	<input type="radio"/>			

Inspection Items	Maker's Shop		On Board		Remarks
	C	O	C	O	
2) Safety valve setting 3) Operation test 4) Installation			<input type="radio"/>	<input type="radio"/>	At sea trial
12. Air-con & refrigerator, provision plant					
1) System vacuum test				<input type="radio"/>	
2) Safety device test				<input type="radio"/>	At sea trial
3) Running test				<input type="radio"/>	
13. Oily water separator Safety device function			<input type="radio"/>	<input type="radio"/>	
14. Incinerator Safety device function	<input type="radio"/>		<input type="radio"/>	<input type="radio"/>	
15. Emergency fire pump					
1) Shooting test			<input type="radio"/>	<input type="radio"/>	* If engine driven
2) Running test(4hrs)			<input type="radio"/> *	<input type="radio"/> *	
16. Sewage treatment unit Operating & safety device test			<input type="radio"/>	<input type="radio"/>	
17. Bilge suction test (E/R, Hold, Pump Room)			<input type="radio"/>	<input type="radio"/>	
18. F.O/L.O/D.O Purifier					
1) Running test		<input type="radio"/>			
2) Automatic control test				<input type="radio"/>	
3) Safety device test				<input type="radio"/>	
19. Engine room crane					
1) Operation test			<input type="radio"/>	<input type="radio"/>	
2) Load test	<input type="radio"/>	<input type="radio"/>	<input type="radio"/> *	<input type="radio"/>	* 1.0 ton S.W.L, and over
20. Quick closing valve for oil tank Operation test			<input type="radio"/>	<input type="radio"/>	

Inspection Items	Maker's Shop		On Board		Remarks
	C	O	C	O	
21. Inert gas generating system 1) Safety device function 2) Blower capacity test			<input type="radio"/>	<input type="radio"/>	By pitot tube
			<input type="radio"/>	<input type="radio"/>	
22. Power pack for hydro oil system Safety device function	<input type="radio"/>		<input type="radio"/>	<input type="radio"/>	
23. C.P.P system 1) Pipe flushing & hydro test			<input type="radio"/> *	<input type="radio"/>	* Hydro test for class I & II grade pipes
2) Safety device function			<input type="radio"/>	<input type="radio"/>	
3) Operating -Pitch control(remote & manual)			<input type="radio"/>	<input type="radio"/>	
-Pump operating				<input type="radio"/>	
24. Personnel lift(elevator) Safety & operating test			<input type="radio"/> *	<input type="radio"/>	* If certificate requested at contract stage
25. Rudder 1) Stock final, machining/NDT	<input type="radio"/>				Case by case Case by case
2) Pintle/neck bush fitting	<input type="radio"/>	<input type="radio"/>	<input type="radio"/>	<input type="radio"/>	
3) Force fitting of pintle/stock	<input type="radio"/>	<input type="radio"/>	<input type="radio"/>	<input type="radio"/>	
4) Stock/bearing clearance check			<input type="radio"/>	<input type="radio"/>	
6) Tiller fitting			<input type="radio"/>	<input type="radio"/>	
7) Jumping stopper clearance check			*	*	* Record to be submitted
8) Contact area between rudder stock & tiller					
	<input type="radio"/>				
26. Workshop machinery Operation test				<input type="radio"/>	
27. Ship side V/V operation			<input type="radio"/>	<input type="radio"/>	
28. Hydraulic power pack for remote control valves					

Inspection Items	Maker's Shop		On Board		Remarks
	C	O	C	O	
1) Safety device test 2) V/V operation test	○		○ ○	○ ○	

## IV . PIPING

Inspection Items	In Shop		On Board		Remarks
	C	O	C	O	
1. Steam line					Class I & II grade pipes shall be hydro test/ NDT in shop or onboard to meet the class rule requirements.
1) Installation inspection			<input type="radio"/>	<input type="radio"/>	
2) Hydrostatic test	<input type="radio"/>	<input type="radio"/>	<input type="radio"/>	<input type="radio"/>	
2. Air line					
1) Installation inspection			<input type="radio"/>	<input type="radio"/>	Application for the installation inspection will not be prepared.
2) Hydrostatic test	<input type="radio"/>	<input type="radio"/>	<input type="radio"/>	<input type="radio"/>	
3. Feed water line for boiler					
1) Installation inspection			<input type="radio"/>	<input type="radio"/>	
2) Hydrostatic test	<input type="radio"/>	<input type="radio"/>	<input type="radio"/>	<input type="radio"/>	
4. Heating coil in tanks					
Hydrostatic test or air test			<input type="radio"/>	<input type="radio"/>	
5. F.O supply lines					
1) Installation inspection			<input type="radio"/>	<input type="radio"/>	
2) Hydrostatic test	<input type="radio"/>	<input type="radio"/>	<input type="radio"/>	<input type="radio"/>	
6. F.O transfer line air test or hydro test			<input type="radio"/>	<input type="radio"/>	
7. Cargo line, Stripping line, Tank cleaning line, Crude oil washing line					
1) Installation inspection			<input type="radio"/>	<input type="radio"/>	
2) hydrostatic test			<input type="radio"/>	<input type="radio"/>	
8. Main engine L.O line, stern tube L.O line, Camshaft L.O line flushing				<input type="radio"/>	
9. Pipe line in living quarter					
Flooding or leak test				<input type="radio"/>	
10. OX/AC line					
Leak test with installation inspection			<input type="radio"/>	<input type="radio"/>	

## V . ELECTRIC

Inspection Items	Maker's Shop		On Board		Remarks
	C	O	C	O	
1. Main generator					
1) Shop test	<input type="radio"/>	<input type="radio"/>			
2) Insulation resistance test (Cold & Hot condition)			<input type="radio"/> *	<input type="radio"/> *	* Record to be submitted
3) Parallel operation test			<input type="radio"/>	<input type="radio"/>	
4) Governor test			<input type="radio"/>	<input type="radio"/>	
5) Auto control test			<input type="radio"/>	<input type="radio"/>	
6) Safety device test for generator engine			<input type="radio"/>	<input type="radio"/>	
7) Load characteristic test			<input type="radio"/>	<input type="radio"/>	
2. Emergency generator					
1) Shop test	<input type="radio"/>	<input type="radio"/>			
2) Insulation resistance test (Cold & Hot condition)			<input type="radio"/> *	<input type="radio"/> *	* Record to be submitted
3) Governor test			<input type="radio"/>	<input type="radio"/>	
4) Safety device test for generator engine			<input type="radio"/>	<input type="radio"/>	
5) Load characteristic test			<input type="radio"/>	<input type="radio"/>	
3. Shaft generator					
1) Shop test	<input type="radio"/>				
2) Insulation resistance test			<input type="radio"/> *	<input type="radio"/> *	* Record to be submitted
3) Safety device test			<input type="radio"/>	<input type="radio"/>	
4) M/E holding R.P.M			<input type="radio"/>	<input type="radio"/>	
5) Parallel operation test			<input type="radio"/>	<input type="radio"/>	
6) Load characteristic test			<input type="radio"/>	<input type="radio"/>	
4. Main switch board					
1) Fabrication & shop test	<input type="radio"/>	<input type="radio"/>			
2) Generator protection test			<input type="radio"/>	<input type="radio"/>	
a. Over current trip					
b. Reverse power trip					
c. Preferential trip					
d. Under voltage trip					

Inspection Items	Maker's Shop		On Board		Remarks
	C	O	C	O	
3) Safety alarm test			<input type="radio"/>	<input type="radio"/>	At sea trial
a. Low/high voltage alarm					
b. Low/high frequency					
4) Black out test with sequential start test			<input type="radio"/>	<input type="radio"/>	
5) Interlock test			<input type="radio"/>	<input type="radio"/>	
5. Emergency switchboard					
1) Fabrication & shop test	<input type="radio"/>	<input type="radio"/>			
2) Generator protection device test			<input type="radio"/>	<input type="radio"/>	
a. Over current trip					
b. Under voltage trip					
6. Bow thruster			<input type="radio"/>	<input type="radio"/>	
1) Safety device			<input type="radio"/>	<input type="radio"/>	
2) Pitch control test				<input type="radio"/>	
3) Operation					
7. Stand by auto starting of auxiliary machine			<input type="radio"/>	<input type="radio"/>	
8. Sensor test					
1) Pressure sensor test			<input type="radio"/>	<input type="radio"/>	
2) Temperature sensor test			<input type="radio"/>	<input type="radio"/>	
3) Level sensor test			<input type="radio"/>	<input type="radio"/>	
9. Lighting equipment function					
1) Navigation & signal light			<input type="radio"/>	<input type="radio"/>	
2) Emergency light			<input type="radio"/>	<input type="radio"/>	
3) Day time signal light			<input type="radio"/>	<input type="radio"/>	
10. Communication equipment and alarm system					
1) Auto telephone				<input type="radio"/>	
2) Sound power telephone			<input type="radio"/>	<input type="radio"/>	
3) Public addressor & talk back system			<input type="radio"/>	<input type="radio"/>	
4) Fire detection system			<input type="radio"/>	<input type="radio"/>	
5) General alarm			<input type="radio"/>	<input type="radio"/>	
6) CO <sub>2</sub> alarm/Foam alarm			<input type="radio"/>	<input type="radio"/>	
7) Extension alarm			<input type="radio"/>	<input type="radio"/>	
8) Engine order telegraphy			<input type="radio"/>	<input type="radio"/>	

Inspection Items	Maker's Shop		On Board		Remarks
	C	O	C	O	
9) Rudder angle indicator			<input type="radio"/>	<input type="radio"/>	
10) Em' cy engineer call			<input type="radio"/>	<input type="radio"/>	
11) Hospital call/Ref. chamber call			<input type="radio"/>	<input type="radio"/>	
11. Navigation equipment					
1) Whistle			<input type="radio"/>	<input type="radio"/>	
2) Magnetic compass				<input type="radio"/>	
3) Gyro compass, autopilot				<input type="radio"/>	
4) Searching Equipment				<input type="radio"/>	
5) Electric clock					
6) Navigator					
7) Automatic identification system			<input type="radio"/>	<input type="radio"/>	
8) Voyage data recorder			<input type="radio"/>	<input type="radio"/>	
12. Radio equipment					
1) Radio telegraph plant			<input type="radio"/> *	<input type="radio"/>	* On behalf of government
2) V.H.F telephone			<input type="radio"/> *	<input type="radio"/>	
3) Satellite communicator			<input type="radio"/> *	<input type="radio"/>	
4) Communal aerial system				<input type="radio"/>	
5) Ship security alert system				<input type="radio"/>	
13. Insulation resistance test for main circuits			*	*	* Record to be submitted
14. Emergency stop for F.O pumps & ventilation fan			<input type="radio"/>	<input type="radio"/>	
15. E/R, Accommodation, on deck cable installation inspection			<input type="radio"/> *	<input type="radio"/> *	* Application for the inspection will not be prepared except behind of wall pannel or ceiling
16. Battery charger function			<input type="radio"/> *	<input type="radio"/> *	* If over 5kw
17. Dead ship start			<input type="radio"/>	<input type="radio"/>	
18. Reef. Com. Monitoring system check				<input type="radio"/>	
19. MGPS/ICCP				<input type="radio"/>	



## VI . PAINTING

Location	Stage	Inspection Witnessed by			
		Block		Hull	
	Item	Surface preparation	Finish After final coating	Surface preparation	Finish After final coating
Flat & Side bottom		O.Q.M	O.Q.M	O.Q.M	O.Q.M
Topside		O.Q.M	Q.M	O.Q.M	O.Q.M
Main deck		O.Q.M	Q.M	O.Q.M	O.Q.M
Accommodation outside		O.Q.M	O.Q.M	O.Q.M	O.Q.M
W.B. tanks		O.Q.M	O.Q.M	O.Q.M	O.Q.M
F.W. tanks		-	-	O.Q.M	O.Q.M
Cargo holds		O.Q.M	O.Q.M	O.Q.M	O.Q.M
Cargo tanks (where to be coated)		O.Q.M	O.Q.M	O.Q.M	O.Q.M
<p>O : Owner supervisor  Q : Q.A Inspector  M : Paint maker supervisor</p> <p>Note : 1. In general, the Owner supervisor shall have free access to monitor the progress of workmanship provided that it does not disturb the work to SHI.  2. The others except above mentioned shall be inspected by the Builder' s QA inspectors and/or paint manufacture' s supervisors.</p>					

## **SAMSUNG SHIPBUILDING QUALITY STANDARD**

---

**Published by**

**SAMSUNG  
HEAVY INDUSTRIES**



SAMSUNG HEAVY INDUSTRIES CO., LTD. GEOJE SHIPYARD  
QUALITY ASSURANCE DEP'T  
530, JANGPYEONG-RI, SHINHYUN-EUP, GEOJE-SI,  
GYEONGSANGNAM-DO, 656-710 KOREA

TEL : +82-55-630-3550/3541

FAX : +82-55-630-4686

<http://www.shi.samsung.co.kr>